

## Synthesis of N-benzothiazole derivative imide on polymeric chain, have possible biological activity

*Entesar O.AL-Tamimi*<sup>\*</sup>, *Mohmoud A-AL-Issa*<sup>\*\*</sup>  
*Hind F-AL-Gburi*<sup>\*\*</sup>

Received 17, September, 2012

Accepted 9, December, 2012

### Abstract:

**In this reserch** Some new substituted and unsubstituted poly imides compounds. were synthesized by reaction of acrylol chloride with different amides (aliphatic and aromatic) in a suitable solvent in the presence amount triethyl amine (Et<sub>3</sub>N) with heating. The Structure confirmation of all polymers were confirmed using FT-IR, <sup>1</sup>H-NMR, <sup>13</sup>C-NMR and UV spectroscopy. Thermal analysis (TG) for some polymers showed their thermal stabilities. Other physical properties including softening points, melting point and solubility of the polymers were also measured

**Key word:**2-aminobenzothiazol,acrylol chloride.

### Introduction

A heterocyclic compound is one which possesses a cyclic structure with at least two different kinds of hetero atoms in the ring. Nitrogen, oxygen and sulphur are the most common hetero atoms. Benzothiazole is a heterocyclic compound, weak base, having varied biological activities and still of great Scientific interest nowa days. They are widely found in bioorganic and medicinal chemistry with application in drug discovery[1]. Benzothiazole moieties are part of compounds showing numbering biological activities such as antimicrobial [2-6], anticancer [7-11], antilmintic and anti-diabetic activities. Polyimides have been widely used as high temperature insulators and dielectrics, coatings, adhesives and materials in a variety of advanced technologies related to microelectronics, where miniaturization and large-scal integration are important technical issues [13-14]. Then high thermal stability and balanced mechanical and

electrical properties [15-17]. Polyimides are mainly used in the aerospace and electronics industries in the form of film and mouldings, but high melting point and insolubility in organic solvent limited their [18-20], application. furthermore,few successful attempts have been made to convert or modify some specific N-substituted imide to serve as ion exchange resins, such as cross linked poly[N-phenyl maleimide] which was prepared by free radical polymerization of the corresponding imide in benzene. The precipitated polyimides were hydrolyzed to obtain some pendant carboxylic groups on the polymeric chains. The last compounds were found to be useful cationic [21] exchange resins of good capacities.

### Materials and Methods

#### General

1. Melting points were recorded by using Gallen Kamp MFB-600 capillary melting point apparatus.
2. FT-IR spectra were recorded using solid KBr discs by testing

\*Department of Chemistry, College of Science, University of Baghdad, Iraq

\*\*Department of Chemistry, College of Science for Woman, University of Baghdad, Iraq

Shimadzu FT-IR 8000 series Fourier transform, infrared spectrophotometer.

- Thermal analyses were performed using thermal analysis system consisting from TG<sub>50</sub> Shimadzu, Japan. Ibn Sina in Iraq.
- <sup>1</sup>H-NMR and <sup>13</sup>C-NMR spectra. Company Bruker, model ultra shield 300MHz, were made at the Chemistry Department, Al-Albyt University, Jordan.

### 1. Preparation of 2-aminobenzothiazole Derivatives[22, 23]

In a 250 ml round bottomed flask equipped with a magnetic bar stirrer and dropping funnel, a solution of bromine (1.2 ml) in glacial acetic acid (75 ml) was allowed to run through the dropping funnel drop wise during 30 min. To a mixture of Para substituted aromatic amine (0.03 mol) and ammonium thiocyanate (0.1 mol) in 150 ml glacial acetic acid with stirring. The mixture was stirred for 1 hr., then diluted with water and neutralized with solid sodium hydroxide. The precipitated substance was filtered, triturated and recrystallized from a suitable solvent to obtain 2-amino benzothiazole derivatives. The physical properties of the synthesized compounds are given in Table (1).

### 2. General Procedure Preparation of 2-[N-(sub or unsub benzoyl and sub or unsub acetyl)amidyl sub benzothiazole]

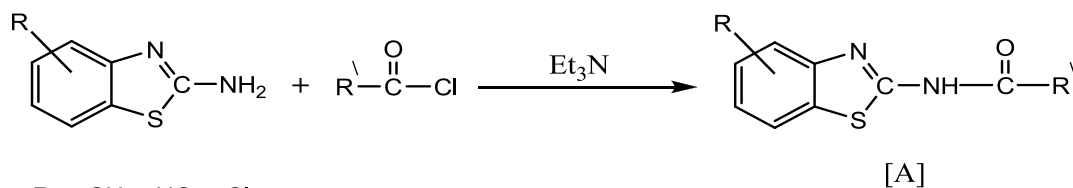
In a round bottom flask equipped with a magnetic bar stirrer and reflux condenser was placed a mixture of sub-benzoyl chloride (0.06 mol) and (0.06 mol) 6-sub-2-aminobenzothiazole with (3) drops of triethyl amine (Et<sub>3</sub>N) in (25 ml) of suitable solvent (Benzene) and refluxed (1-3) hrs after the solvent was removed and recrystallized from ethanol.

### 3. General Procedure Preparation of Poly 2-(N-acryl-N-sub or unsub benzoyl) imidyl Substituted Benzothiazole


In a round bottom flask equipped with a magnetic bar stirrer was placed a mixture of poly (acryloyl chloride) (0.06 mol) and (0.06 mol) of 2-N-sub amidyl-sub benzothiazole with (1 ml) of triethyl amine (Et<sub>3</sub>N) in (25 ml) of suitable solvent (THF or DMF) and refluxed for (5-7) hrs. after cooling and removed the solvent. The solid separated was filtered and purified by dissolving at DMF or DMSO and re precipitating from water or acetone. This procedure was applied on compounds as shown in Table (1). All physical properties are listed in Table (1).

## Results and Discussion

### Preparation of [2-(N-benzoyl) amidyl sub benzothiazole]




R = CH<sub>3</sub>, NO<sub>2</sub>, Cl




All poly [2-(N-acryl-N-benzoyl) imidyl substituted benzothiazole. were prepared by the reaction of poly

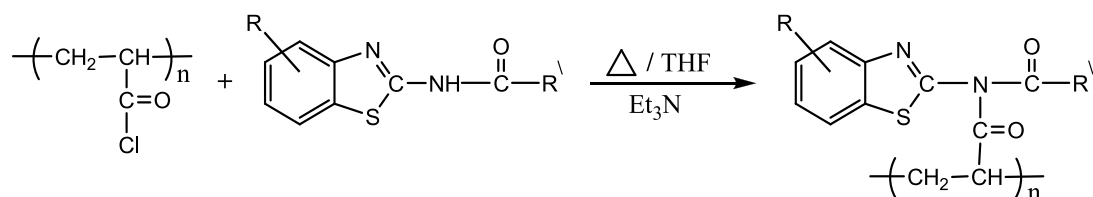(acryloyl chloride) with different amides . in presence



of triethyl amine ( $\text{Et}_3\text{N}$ ) as a catalyst [24]. All these compounds characterised by (FT.IR, UV, and softing point), Table(1).

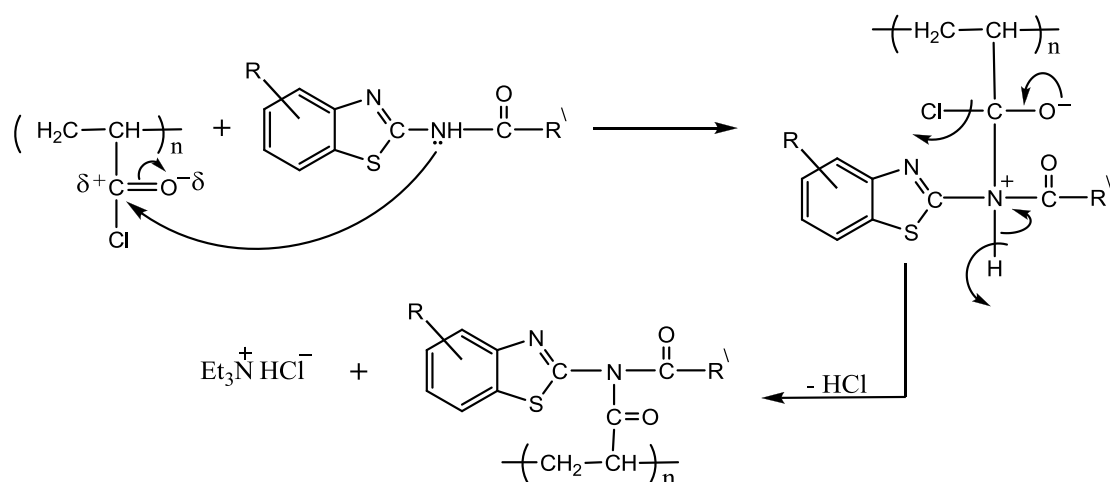The mechanism of reaction involves a nucleophilic attack on the carbonyl as shown below [25].









Structures confirmation of all prepared polymer proved using FT-IR, UV,  $^1\text{H-NMR}$ ,  $^{13}\text{C-NMR}$ , TG and physical properties including softening point, solubility, Tg and percent conversion of the polymers. FT-IR spectrum of compounds showed the same bands appearance. Stretching band at  $1670\text{cm}^{-1}$   $\nu(\text{C}=\text{O})$ ,  $(2800-2920)\text{cm}^{-1}$   $\nu(\text{C-H})$  aliphatic,  $(1590-1630)\text{cm}^{-1}$   $\nu(\text{C}=\text{C})$  and  $(3010-3100)\text{cm}^{-1}$   $\nu(\text{C-H})$  aromatic as shown Table (2).  $^1\text{H-NMR}$  spectrum of polymers [3,4,5] showed the signals at  $\delta(1.2)$  (t, 2H,  $-\text{CH}_3$ ),  $\delta(3.1)$  (m, 1H,  $-\text{CH}_2-$ ) while a signal at  $\delta(7-8)$  (d or m, 1H, Ph-H) and  $\delta 1.02$  (s, 3H, Ph- $\text{CH}_3$ ), as shown listed in Table (3). The  $^{13}\text{C-NMR}$

spectrum of compound showed the signal at  $(170-180)\text{ppm}$  for carbonyl group ( $\text{C}=\text{O}$ ) and appeared at  $(120-140)\text{ppm}$  and appeared at  $(20-50.48)\text{ppm}$ . UV spectrum of compounds absorption  $\lambda_{\text{max}}$  at  $300\text{nm}$  and  $380\text{nm}$  which attributed to  $(\pi \rightarrow \pi^*)$  and  $(n \rightarrow \pi^*)$  transitions. See Table (4). TG analysis provides a change in the mass of the polymer during heating. The thermal analysis was carried out at temperatures  $(200-400)^\circ\text{C}$  with heating rate  $20.0^\circ\text{C}/\text{min}$ . in  $\text{N}_2$  atmosphere. Thermal stability of the product was estimated from TG and DTG thermograms. See Table (5), it was found that the prepared polymers high stability, resists to isomerization by

heat, light or using acidic or basic solution[26,27].

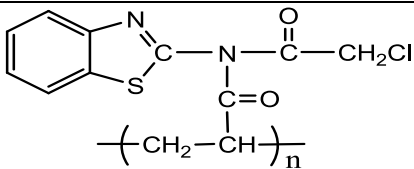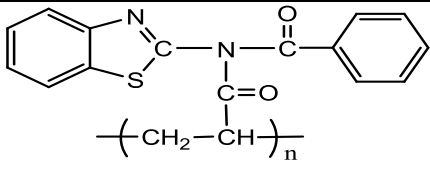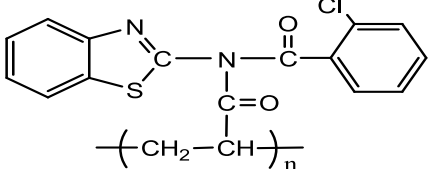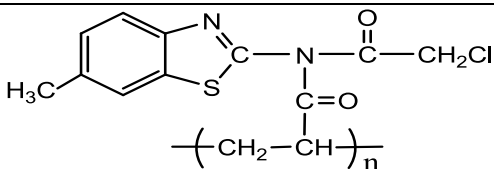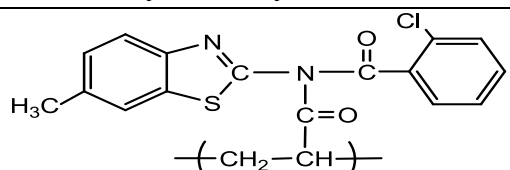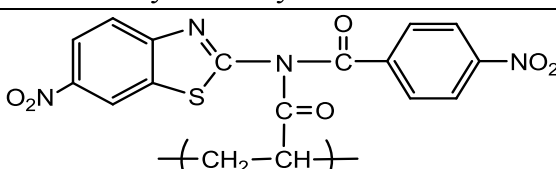**Table (1): Physical properties of the poly imide**

Comp. No.	Compound structure	Conversion %	Softing point °C	Color	Solvent used in reaction
1	 <p>Poly [2-(N-acryl-N-chloroacetyl)imidyl benzothiazole]</p>	75	120-135	Brownish yellow	THF or DMF
2	 <p>Poly [2-(N-acryl-N-benzoyl)imidyl benzothiazole]</p>	80	120-135	Brownish yellow	THF or DMF
3	 <p>Poly [2-(N-acryl-N-2-chlorobenzoyl)imidyl benzothiazole]</p>	82	125-140	Brownish yellow	THF or DMF
4	 <p>Poly [2-(N-acryl-N-chloroacetyl)imidyl-6-methyl benzothiazole]</p>	78	112-125	Light yellow	THF or DMF
5	 <p>Poly [2-(N-acryl-N-2-chlorobenzoyl)imidyl-6-methyl benzothiazole]</p>	85	120-132	Light yellow	THF or DMF
6	 <p>Poly [2-(N-acryl-N-4-nitrobenzoyl)imidyl-6-nitro benzothiazole]</p>	80	200-205	Light yellow	THF or DMF

7	<p>Poly [2-(N-acryl-N-acetyl) imidyl-4,6-di-chloro benzothiazole]</p>	78	85-100	Light yellow	THF or DMF
Comp. No.	Compound structure	Conversion %	Softing point °C	Color	Solvent used in reaction
8	<p>Poly [2-(N-acryl-N-acetyl) imidyl-2,4-di-chloro benzothiazole]</p>	70	170-180	Light yellow	THF or DMF
9	<p>Poly [2-(N-acryl-N-benzoyl)imidyl -4-nitro-6-chloro benzothiazole]</p>	85	95-105	Brown	THF or DMF
10	<p>Poly [2-(N-acryl-N-acetyl) imidyl-6-chloro benzothiazole]</p>	87	125-142	Brown	THF or DMF
11	<p>Poly [2-(N-acryl-N-2-mercaptobenzoyl) imidyl-6-chloro benzothiazole]</p>	85	170-180	Brown	THF or DMF
12	<p>Poly [2-(N-acryl-N-2-mercaptobenzoyl) imidyl-6-methyl benzothiazole]</p>	82	130-140	Light yellow	THF or DMF

Table (2): FT-IR spectra of the prepared heterocyclic polyimide

Comp. No.	Compound structure	FTIR spectral data $\text{cm}^{-1}$							
		$\nu(\text{C=O})$ imide	$\nu(\text{C-N})$ imide	$\nu(\text{C=C})$ aromatic	$\nu(\text{C-H})$ aliphatic	$\nu(\text{C-H})$ aromatic	$\nu(\text{C=N})$ imine	$\nu(\text{C-S})$	Others
1		1697	1410	1590	2900 2970	3010	1500	680	C-Cl 1010
2		1690	1420	1610	2905 2975	3000	1520	700	-
3		1685	1460	1600	2900	3000	1510	650	C-Cl 1000
4		1690	1400	1640	2890 2920	3100	1550	700	C-Cl 1005
5		1682	1480	1610	2945	3100	1500	650	C-Cl 1010
6		1685	1440	1640	2900	3010	1520	600	C-Cl 1100
7		1699	1400	1640	2945 2980	3020	1550	779	C-Cl 1157
8		1716	1431	1635	2947 2975	3074	1535	779	C-Cl 1157
9		1708	1400	1543	2943 2978	3100	1543	750	C-Cl 1037 C- NO2 1346
10		1695	1410	1600	2945 2985	3105	1540	650	C-Cl 1020
11		1697	1446	1636	2943 2978	3062	1535	763	C-Cl 1037

12		1700	1430	1620	2949 2980	3010	1510	610	-
----	--	------	------	------	--------------	------	------	-----	---

Table (3): The <sup>1</sup>H-NMR chemical shifts of some of the prepared poly heterocyclic imides

Comp. No.	Compound structure	Chemical shifts
3		$\delta$ 1.2 (t, 2H <sup>2</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 3.01 (m, 1H <sup>1</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 7-8 (m, HAr)
4		$\delta$ 1.1 (s, 3H <sup>4</sup> ); $\delta$ 1.1 (t, 2H <sup>2</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 3.1 (m, 1H <sup>1</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 4.5 (s, 2H <sup>7</sup> ); $\delta$ 7-8 (m, HAr)
5		$\delta$ 1.2 (s, 3H <sup>4</sup> ); $\delta$ 1.2 (t, 2H <sup>2</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 3 (m, 1H <sup>1</sup> , $(-\text{H}_2\text{C}-\text{CH})_n$ ); $\delta$ 7-8 (m, HAr)

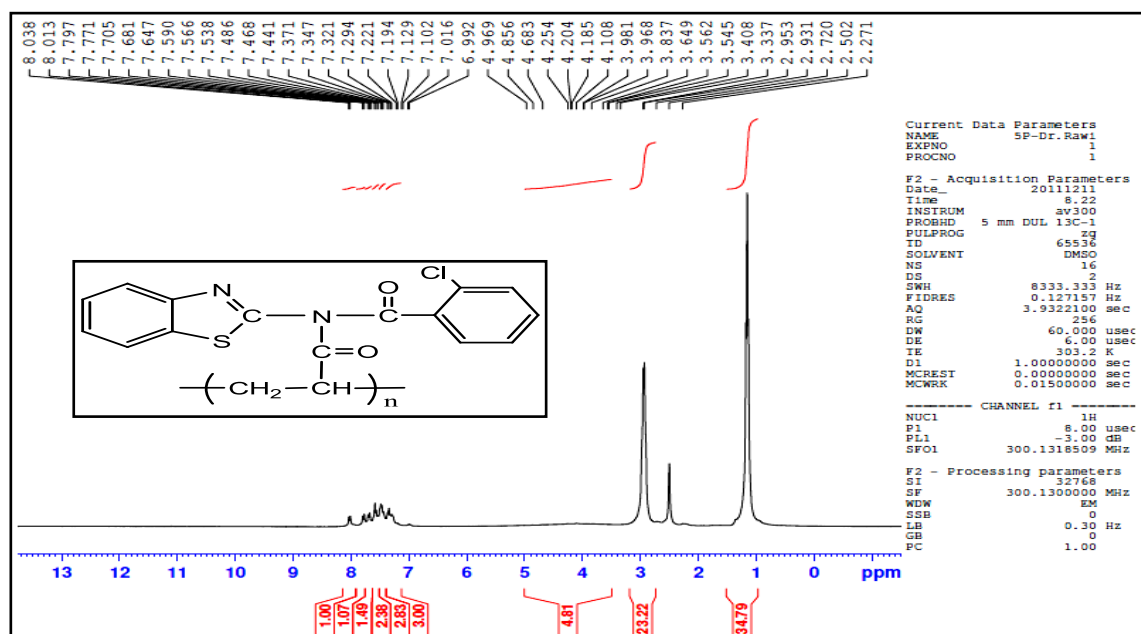


Fig.(1): <sup>1</sup>H-NMR for compound[3]

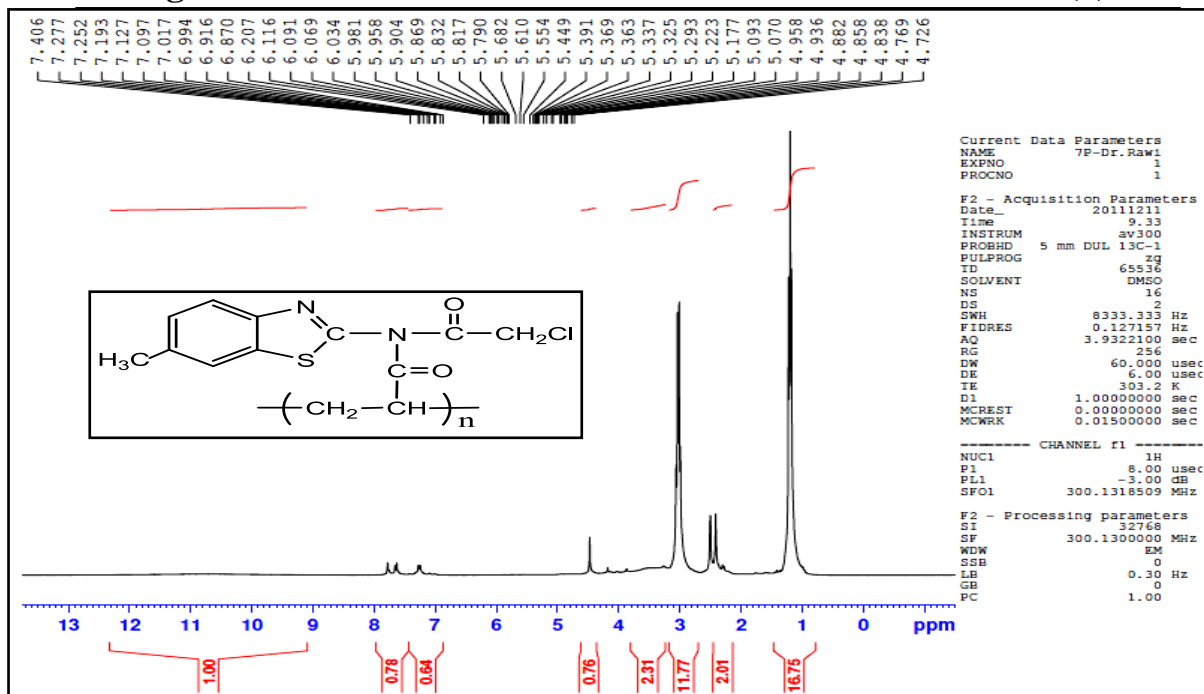


Fig.(2): <sup>1</sup>H-NMR for compound[4]

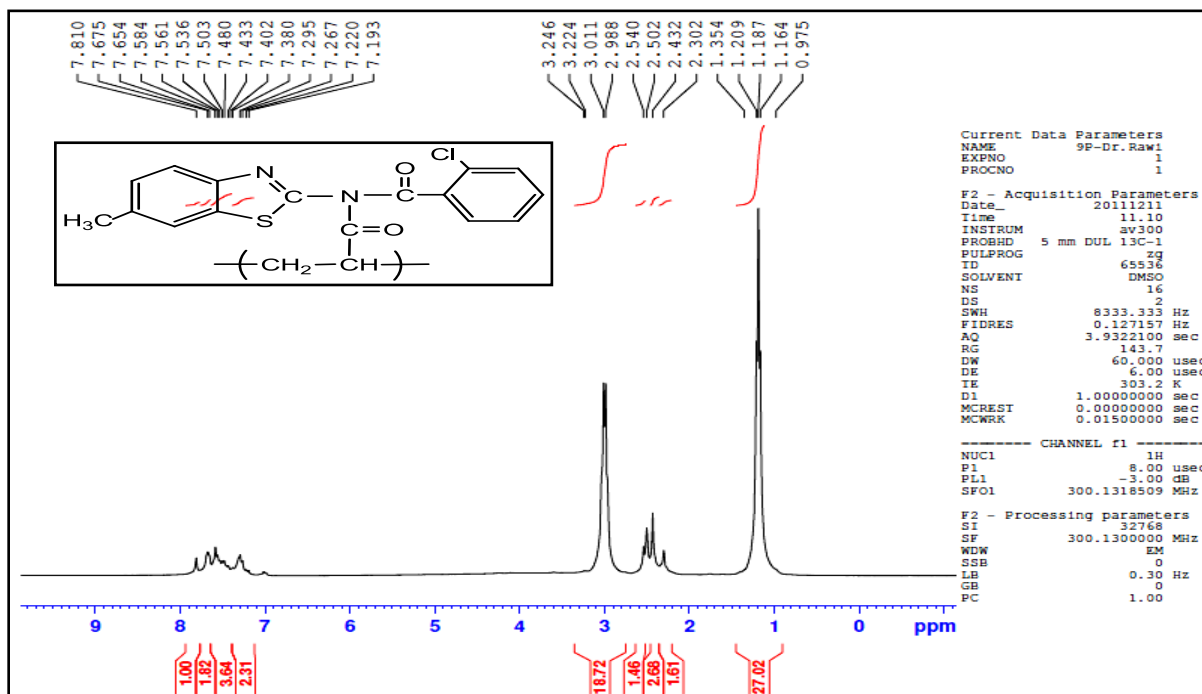


Fig.(3): <sup>1</sup>H-NMR for compound[5]



Table (4): UV spectra of the prepared heterocyclic polyimide













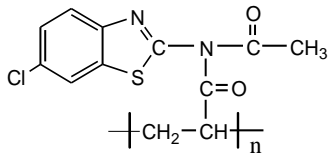
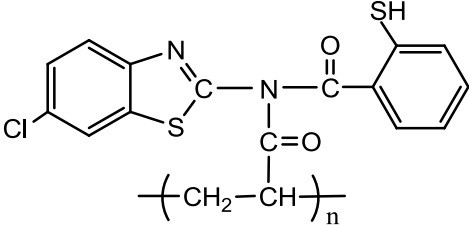
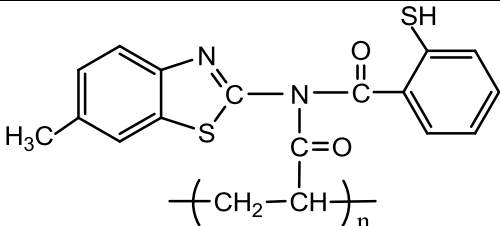
Comp. No.	Compound structure	Peak	
		$\lambda_{\max}$ nm	ABC
1		301	1.336
2		317 459.5	1.362 0.035
3		370	1.22
4		303.5	1.724
5		317	1.272
6		435.5 361.0	0.716 1.099
7		315	2.298
8		303.5 248	0.752 0.053
9		409.5 303	0.76 0.913
10		305	1.747
11		315.5 454	1.195 0.068
12		316 449.5	1.225 0.01

Table (5) : TG of some of the prepared poly heterocyclic imides

Comp. No.	Compound structure	10% wt Loss temp °C	50% wt Loss temp °C	Peak 1 Temp °C	Peak 2 Temp °C
10		177.39	266.63	180.9	253 392
11		175.21	341.7	279.95	339 384.8
12		189.65	269	236	286.8 377.9

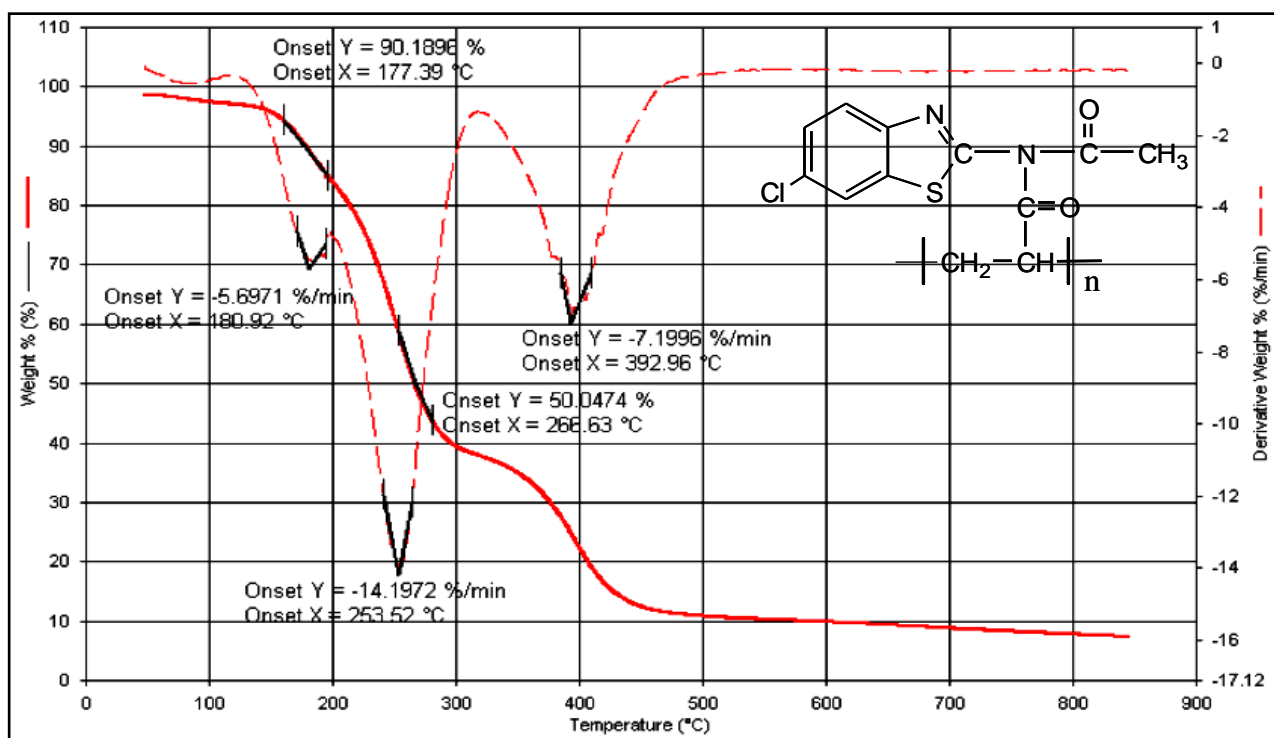


Fig.(4): TG for compound[10]

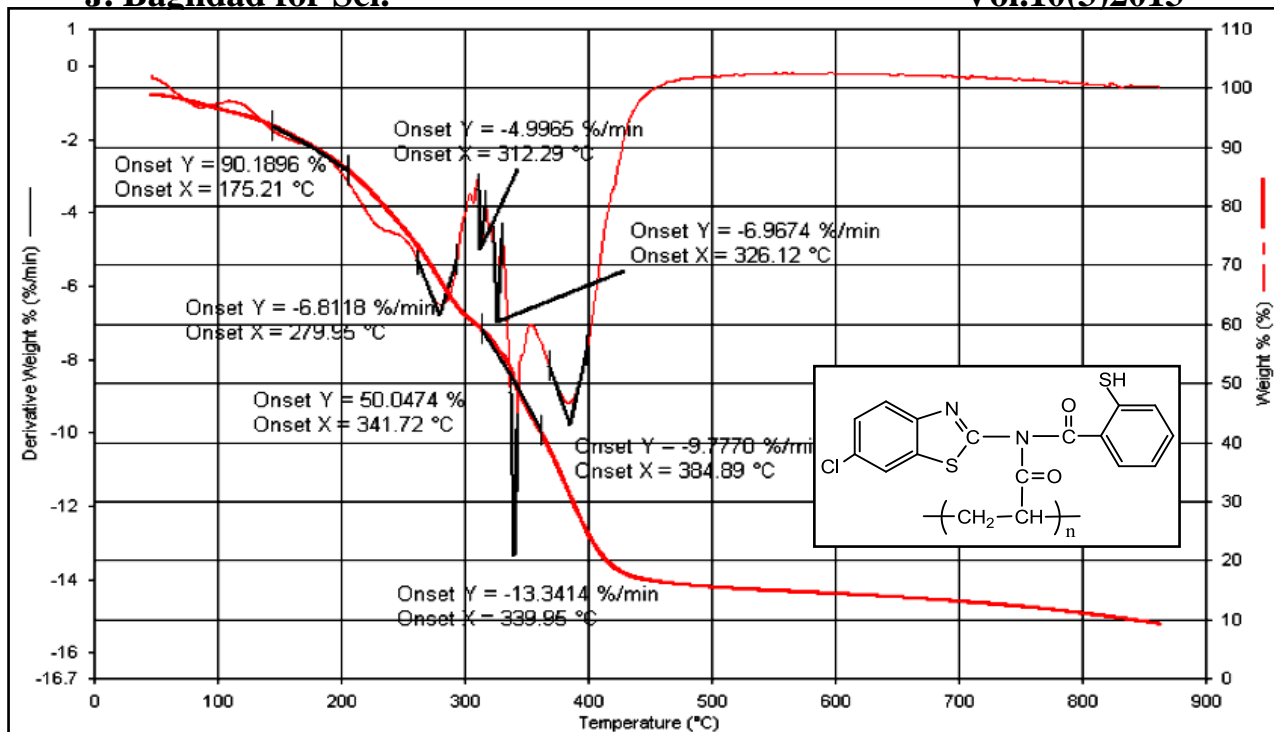


Fig.(5): TG for compound[11]

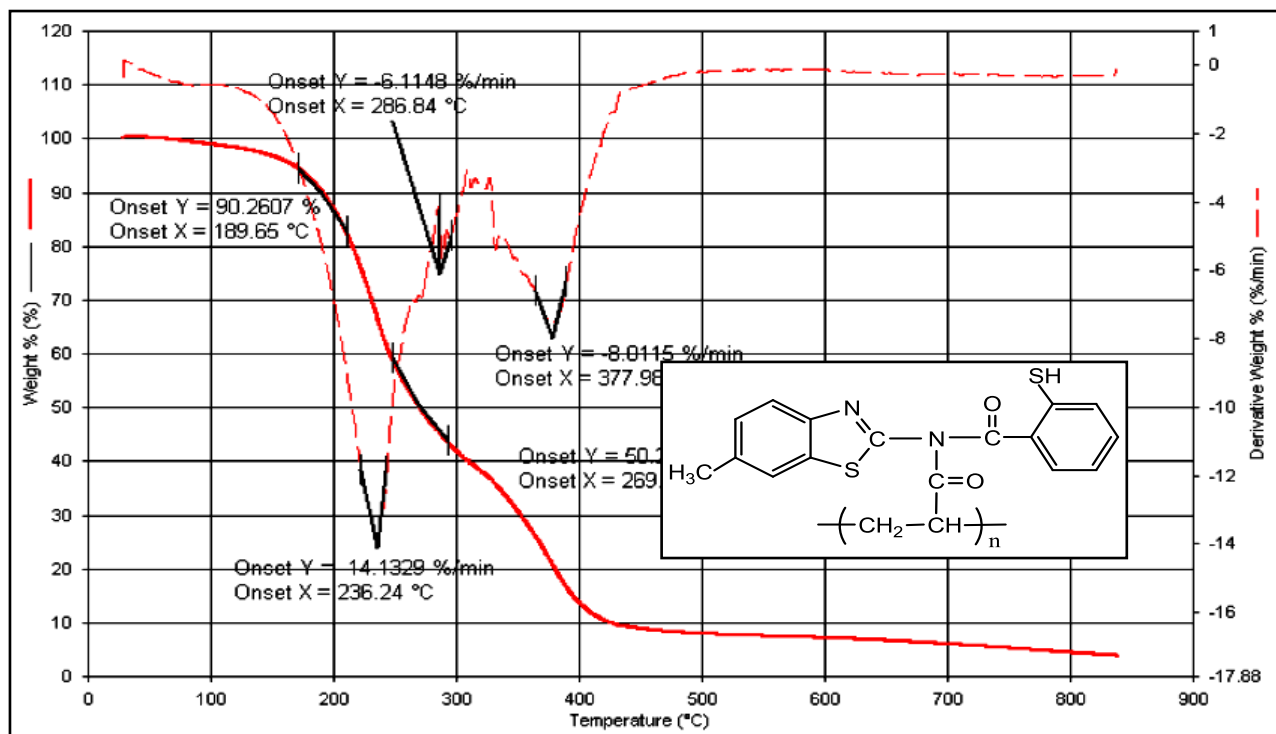


Fig.(6): TG for compound[12]

References 1. Yadav.P.S and Senthilkumar.D.G.P. 2011.

- "Benzothiazole: Different methods of synthesis and diverse biological activities". IJPSDR., 3(1): 1-7.
- Gupta.S, Ajmera,N. Gautam,N. Sharma.R. and Gautam.D. 2009. "Novel synthesis and biological activity study of pyrimido[2,1-b]benzothiazoles". Ind. J. Chem., 48B: 853-858.
  - Kumbhare, R.M. Ingle.V.N. 2009. "Synthesis of novel benzothiazole and benzisoxazole functionalized unsymmetrical alkanes and study of their antimicrobial activity". Ind. J. Chem., 48B: 996-1000.
  - Muthi.Y, and Pathak.D. 2008"Synthesis and antimicrobial screening of substituted 2-mercaptobenzothiazoles".J Pharm Res.7(3);153-155
  - Rajeeva,B, Srinivasulu.N. and Shantakumar.S 2009. "Synthesis and antimicrobial activity of some new 2-substituted benzothiazole derivatives. E-journal of chemistry., 6(3): 775-779.
  - Maharan.M . William.S . Ramzy.F and Sembel.A. 2007. "Synthesis and in vitro evaluation of new benzothiazole derivatives as schistosomicidal agents". Molecules., 12: 622-633.
  - Kini S. Swain.S and Gandni.A 2007. "Synthesis and evaluation of novel benzothiazole derivatives against human cervical cancer cell lines". Ind. J. Pharm. Sci., Jan-Feb: 46-50.
  - Stanton.H , Gambari.R, Chung.H.C, Johnny.C, Filly.C, and Albert.S 2008. "Synthesis and anticancer activity of benzothiazole containing phthalimide on human carcinoma cell lines". Bioorg. Med. Chem., 16: 3626-3631.
  - Wang. M, Gao.M , Mock B, Miller.K, Siedge, G, Hutchins.G and Zheng.Q,2006. "Synthesis of E<sub>11</sub> labelled flulorinated 2-aryl benzothiazoles as novel potential PET cancer imaging agent". Bioorg. Med. Chem., 14: 8599-8607.
  - Gupta.S , Moorthi.N and Sanyal.U 2010. "Synthesis, cytotoxic, evaluation, in silico pharmacokinetic and QSAR study of some benzothiazole derivatives". Ind. J. Pharmacy pharm. Sci., 2(3): 57-62.
  - Sreenivasa.M. Jaychand.E ShivakumarB, Jayraj Kumar.K and Vigaykumar.J.2005. "Synthesis of bioactive molecule flurobenzothiazole comprising potent heterocyclic moieties for anthelmintic activity". Ind. J. Chem., 44B: 2404-2408.
  - Pattan.S, Suresh.C, Pujar.V Reddy.V, Rasal.V and Koti.B 2005. "Synthesis and antidiabetic activity of 2-amino[5(4-sulphonyl benzylidene)-2,4-thiazolidine none]-7-chloro-6-flouro benzothiazole. Ind. J. Chem., 44B: 2404-2408.
  - Omote.T. 1996."Polyimide-fundamentals and application". M. K. Ghosh and K. L. Mittal, Ed. Marcell Dekker. Inc, New York., p.121.
  - Bureau.J.M. and Mittal.J.P. 1996. "Applications of polyimides as photosensitive materials". M. K. Ghoh, K. L. Mittal. Marcel Dekker, New York., p.743.
  - Feger.C, Khojasteh.M.M and Grath.J.E. 1989. Polyimides materials chemistry and characterization amesterdam. Elsevier, 453-478.

16. Wilson.D, Stenzenberger.H.D. and Hergenrother.P.M. 1990. "Polyimide". Glasgow, black., p.360-395.
17. Barikani.M. 2002. " Polyimides derived from diisocyanate". Iran. Polym. J., 11: 215-236.
18. Rozhanskii.I, Okuyama.K. and Goto.K. 2000. "Synthesis and properties of polyimides derived from isomeric biphenyl-tetra carboxylic dianhydrides". Polymer., 41: 7057-7065.
19. Der-jang L. Been-yang.L and Chia-wei.Y. 2001 "Synthesis and characterization of new organosoluble polyimides based on flexible diamine". Polymer .,42:839-845.
20. Tamami.B. and Yeganeh.H. 2001. "Synthesis and characterization of novel aromatic polyimides derived from 4-aryl-2,6-bis(4-aminophenyl)pyridines". Polymer., 42: 415-420.
21. Hussain.S.M.2003. Ph.D. Thesis, College of Science, University of Baghdad.
22. Stuckwisch.C.G. 1949. J. Am. Chem. Soc., 71: 3417.
23. Mahdi.S.A.2008.M.Sc. Thesis, College of Science, University of Baghdad.
24. Carey.F.A and Sundber.R.J. 2007. "Advanced Organic Chemistry Part A: Structure and Mechanisms", 5<sup>th</sup> Ed., New York.
25. Crews.P . Rodriguez.J and Jaspars.M. 1998. "Organic structure analysis", Oxford University Press, New York.
26. Korshak.U.V. 1969. "The Chemical structure and thermal characteristics of polymer".
27. Al-Farajy.G.H.A. 2003. M.Sc. Thesis, College of Science, University of Baghdad.

## (تحضير مشتقات ن\_ بنزو ثايازول ايميد على السلسلة البوليمرية ذات فعالية بايولوجية متوقعة)

هند فاضل الجبوري\*\*

محمود العيسى\*\*

انتصار عبيد التميمي\*

\*كلية العلوم - قسم الكيمياء  
\*\*كلية العلوم للبنات - قسم الكيمياء

### الخلاصة:

في هذا البحث حضر بولي ايميدات جديدة معوضة وغير معوضة من تفاعل بولي كلوريد الاكريلويل مع اميدات مختلفة (اليفاتية , اروماتية) بوجود مذيب مناسب وكمية مناسبة من ثلاثي ميثيل امين (Et<sub>3</sub>N) مع التسخين. وتم اثبات التراكيب الكيميائية للبوليمرات المحضرة باستخدام الطرق الطيفية، اطياف الاشعة تحت الحمراء FT-IR، اطياف الرنين النووي المغناطيسي <sup>1</sup>H-NMR، اطياف <sup>13</sup>C-NMR واطياف الاشعة فوق البنفسجية UV كما تم التعرف على استقرارية بعض البوليمرات المحضرة حرارياً عن طريق التحليل الحرارية بالإضافة الى القياسات الفيزيائية المختلفة من درجات التلين ودرجات الانصهار والذوبانية