

## The Spectroscopic Behaviour of Rhodamine 6G in Liquid and Solid Solutions

*Nathera A.A.Al-Temeem\**

*Salwan K.Jameel\**

*Ahsan A. Abd Alfahdawi\**

Date of acceptance 19/9/2007

### Abstract:

Absorption, fluorescence, quantum yield and lifetime of rhodamine 6G in chloroform, methanol and dimethyl sulfoxide were measured. From a comparison of these quantities, with those for solid solutions (solid solutions are obtained by mixing constant volume proportions of dye at a concentration of  $1 \times 10^{-4}$  M/l with different volume proportions from the concentrated solution of polymer in chloroform and dimethyl sulfoxide).

The results showed that the addition of polymer to liquid concentrated solutions ( $1 \times 10^{-4}$  M/l) of rhodamine 6G dye from expecting [which leading to development active medium for laser dye at high concentration] increase the spectra shift toward high energies, and the luminescence quantum yield but decreasing radiative lifetime.

### Introduction:

Along the years dye lasers have demonstrated to be useful and versatile sources of tunable coherent radiation with wide applicability in many different fields<sup>[1]</sup>. Dye oscillators and amplifiers operate under intense optical excitation which results in significant population build up in the lowest excited singlet  $S_1$ . Absorption from  $S_1$  can produce a number of deleterious effects such as reduction of effective gain, interference with optical pumping, and introduction of an extra thermal load due to the energy released as heat in the subsequent relaxation back to  $S_1$ , as well as photochemical reaction, Thus knowledge of the spectral properties of the spectral properties of  $S_1$  state would be necessary to design efficient dye lasers and to determine optimum pumping conditions<sup>[2-9]</sup>.

In this paper we have study the absorption, emission spectra with a different solvents, and, concentrations of Rh6G, firstly as a solution, and secondly as a solid solution when it mixed with PMMA at a different volume.

### Experimental:


The following materials were used:  
- rhodamine 6G ( $C_{28}H_{31}N_2O_3Cl$ ) {Eastman Kodak Com.} which molecular weight is 479.02 g/M as shown the molecular structure in Fig. (1). chloroform, methanol, dimethyl sulfoxide (all analytical grad, Fluka Com.) and PMMA beads (laboratory grade, ICI, Com.).

A series of solutions of Rh6G at concentrations varying from [ $10^{-6}$ -  $10^{-4}$ ] M/l were prepared in chloroform, methanol, and, dimethyl sulfoxide. The solid Solutions were prepared by mixing a constant volume proportion from a concentrated of Rh6G ( $1 \times 10^{-4}$  M/l) with different volume proportions for concentrated solutions of the polymer in chloroform and dimethyl sulfoxide ( $V_{Rh6G}/V_{PMMA}$ = without polymer, 1/0.25, 1/4, 1/8).

The absorption and florescence spectra were measured by using spectrofluorimeter model RF-500, Shimadzu Com. Which illustrated in Fig. (2).

\*Baghdad University, Collage of Science, Physics Department, Baghdad, Iraq

The quantum efficiencies were measured by the comparative method <sup>[10]</sup> using as standard solutions <sup>[11]</sup> {as solution of Rh6G in methanol which has a quantum efficiency of 94% }.

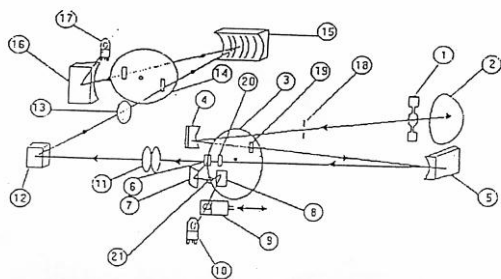

**Fig. (1):- Schematic of experimental apparatus.**

1- Xenon lamp, 2- Condensor ellipsoidal mirror,(Sio<sub>2</sub> coated), 3- Excitation slit assembly, 4- Concave mirror, 5- Concave diffraction grating (for excitation), 6- Beam splitter quartz plate, 7- Teflon reflector No.1, 8- Teflon reflector No.2, 9- Optical attenuator, 10- Monitor photomultiplier, R212-09, 11- A coupl of light-collecting lenses, 12- Cell, 13- Light-collecting lens, 14- Emission slit assembly, 15-Concave diffraction(for emission), 16-Concave mirror, 17- Photometric photomultiplier, R452-01, 18-Focus, 19- Entrance slit, 20-Exit slit, 21-Light beam balancing aperture

## Results and Discussion:

In figures (2, 3, 4) which represents the absorption, emission spectra (A,B,C,a,b,c respectively) of Rh6G in chloroform, methanol, dimethyl sulfoxide for concentrations ( $10^{-4}$ ,  $10^{-5}$ ,  $10^{-6}$  M/l). Absorption maxima, wave numbers, and, lifetime are measured in table (1) <sup>[12]</sup>. Emission maxima, wave numbers, and, quantum efficiencies were measured in table (2). From this figures and tables we can see that there are shift to the low energy (long wave length) as the concentration increases, while the quantum yield decreases and lifetime increases. The

shift in spectra toward long wave length as the concentration is increases. These changes have been interpreted in two different ways. On the one hand there are considered as due to dimerization process <sup>[13-19]</sup>. On the other, they are attributed to the change of RhB from its neutral form (Rh6G<sup>+</sup>) to the cationic one Rh6GH<sup>+</sup> <sup>[20-23]</sup> Fig. (5).

This theory is based on the decreasing of PH produced when dye concentration increases.

The decreasing of quantum yield as the concentration increases, have been interpreted by dimmer molecules which absorb the emission photons. This is due to the band energy of dimer molecules under the band energy of RhB molecules (monomer). These results are agreement with Lopez Arbeloa, and, his team<sup>[24]</sup>.

The decreasing of quantum yield as the concentration increases, have been interpreted by dimmer molecules which absorb the emission photons. This is due to the band energy of dimer molecules under the band energy of Rh6G molecules (monomer). These results are agreement with Lopez Arbeloa, and, his team.


Fig.(6) represent the absorption spectra (A, B) of Rh6G in chloroform, and, dimethyl sulfoxide of concentration  $10^{-4}$ M/l, where it mixed with different proportions from the concentrated solution of polymer in chloroform and dimethyl sulfoxide respectively. The absorption maxima, FWHM and lifetime, are summarized in table (3). Fig. (7) represents emission spectra (a, b) of Rh6G in chloroform and dimethyl sulfoxide of concentration  $10^{-4}$ M/l when it mixed with different proportions from the concentrated solution of polymer in chloroform and dimethyl sulfoxide respectively. Emission maxima, quantum yield of mixed Rh6G solution, and, polymer solutions are summarized in table (4).

From these curves and tables we can get that the addition of the polymer to


concentrated solutions ( $10^{-4}$ M/l)of Rh6G; [from expecting that leading to development active medium for laser dye at high concentrations] where increasing spectra shift toward high energies increasing luminescence quantum yield and decreasing relative radiation lifetime,

either in relation liquid solutions that increasing


Concentration leading to increasing spectra shift toward low energies, decreasing luminescence quantum yield and increasing relative lifetime. These results are agreement with [25-30].

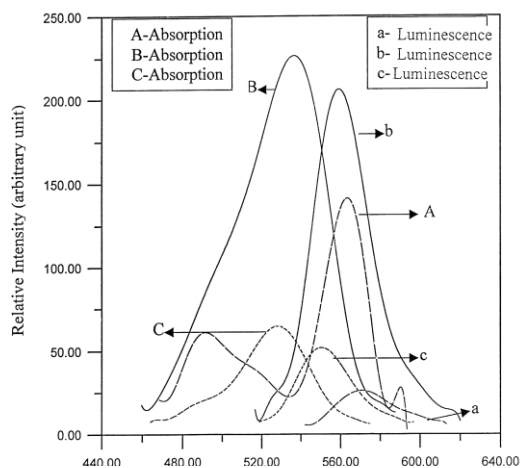

**Fig.(2) :- Absorption, emission spectra (A, B, C, a, b, c) of Rh6G in chloroform for concentration ( $10^{-4}$ ,  $10^{-5}$ ,  $10^{-6}$  M/l)**

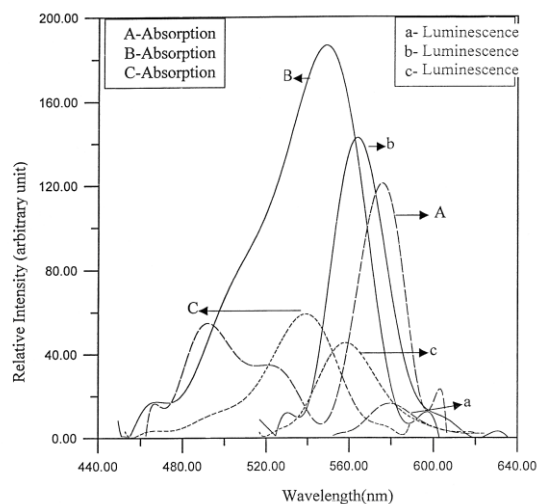

**Fig. (4):- Absorption, emission spectra (A, B, C, a, b,c) of Rh6G in dimethyl sulfoxide for concentration (  $10^{-4}$ ,  $10^{-5}$ ,  $10^{-6}$  M/l).**

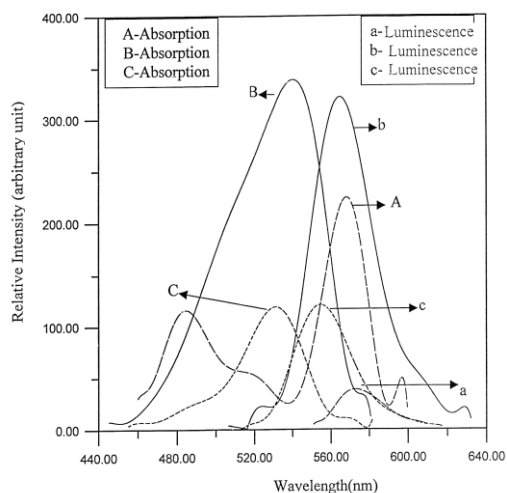


**Fig. (3):- Absorption, emission spectra (A, B, C, a, b, c) of Rh6G in methanol for concentration ( $10^{-4}$ ,  $10^{-5}$ ,  $10^{-6}$  M/l).**

**Table 1: Mole concentration, absorption and emission maxima, and, life time of rhodamine 6G in chloroform, methanol, and, dimethyl sulfoxid.**


Rhodamine 6G						
Solvent	Concentration M/L	$\lambda_{Abs.}$ (nm)	$\bar{\nu}_{Abs.}$ (cm <sup>-1</sup> )	$\lambda_{Flu}$ (nm)	$\bar{\nu}_{Flu}$ (cm <sup>-1</sup> )	$\tau_{FM}$ (ns)
Chloroform	1*10 <sup>-4</sup>	563.8	17736.78	574	17421.6	5.2
	1*10 <sup>-5</sup>	536.15	18651.49	559.9	17860.33	4.1
	1*10 <sup>-6</sup>	531	18832.39	553	18083.18	3.4
Methanol	1*10 <sup>-4</sup>	567.6	17618.04	573.3	17442.87	5.5
	1*10 <sup>-5</sup>	540	18518.51	564.75	17706.94	3.9
	1*10 <sup>-6</sup>	529	18903.59	551	18148.82	3.6
Dimethyl Sulfoxide	1*10 <sup>-4</sup>	576.8	17337.03	580.8	17217.63	6.3
	1*10 <sup>-5</sup>	550.4	18168.6	564	17730.49	4.5
	1*10 <sup>-6</sup>	539.2	18545.99	558.4	17908.3	3.8

**Table 2: Mole concentration, life time, and, quantum yeild of rhodamine 6G in chloroform, methanol, and, dimethyl sulfoxid.**


Rhodamin 6G			
Solvent	Concentration M/l	$\tau_{FM}$ (ns)	Quantum Yield (Q <sub>FM</sub> )
Chloroform	1*10 <sup>-4</sup>	5.2	0.66
	1*10 <sup>-5</sup>	4.1	0.7
Methnol	1*10 <sup>-4</sup>	5.5	0.79
	1*10 <sup>-5</sup>	4.2	0.94
Dimethyl sulfoxide	1*10 <sup>-4</sup>	6.3	0.5
	1*10 <sup>-5</sup>	4.5	0.56

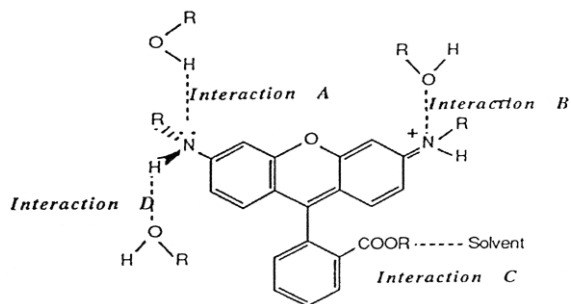


**Fig. (5) Molecular structure of neutral (R6G<sup>+</sup>) and cationic (R6GH<sup>+</sup>) forms of rhodamine B.**

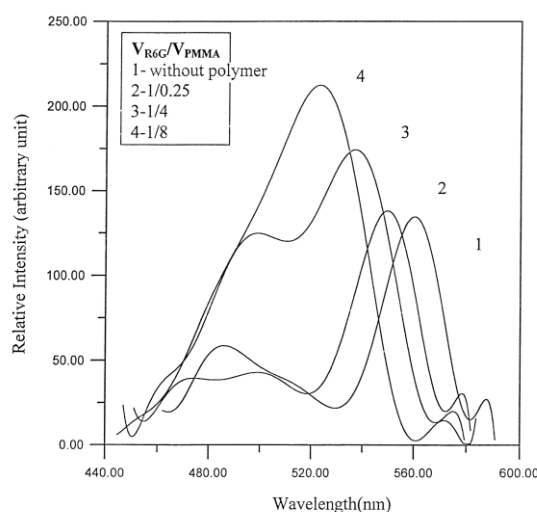

**Fig. (6A):-The absorption spectra of Rh6G in chloroform of concentration 10<sup>-4</sup>M/l, with different volume proportions polymer.**

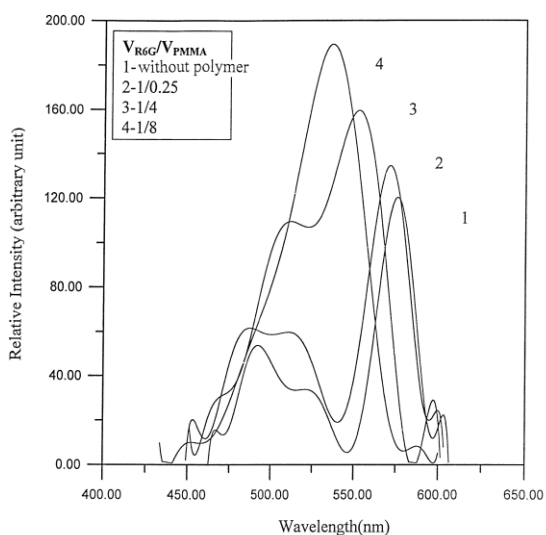


**Fig. (6B):-**The absorption spectra of Rh6G in dimethyl sulfoxide of concentration 10-4M/l with different volume proportions polymer.

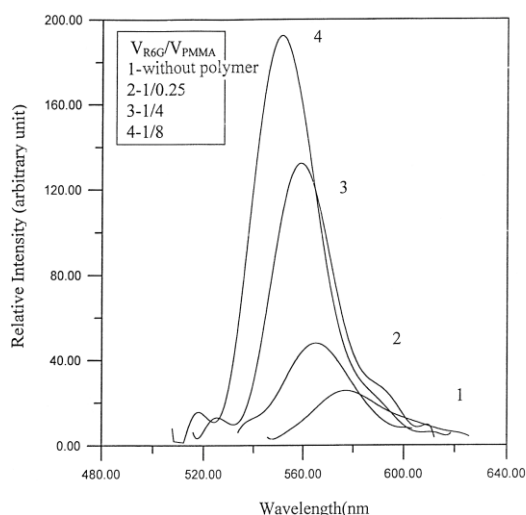

**Fig. (7A):-**The emission spectra of Rh6G in chloroform of concentration 10-4M/l, with different volume proportions of polymer.

**Table 3: Spectro parameters of absorption spectra of rhodamine 6G for concentration 10-4 M/l in chloroform , and, dimethyl sulfoxide with different volume proportions of polymer.**

Rhodamin 6G					
Solvent	$V_{RB}/V_{PMMA}$	$\lambda_{Abs.}$ (nm)	$I_{(max.)Abs.}$	$\Delta \lambda_{Abs.}$ At FWHM (nm)	$\tau_{FM}$ (ns)
Chloroform	Without polymer	563.8	139.5	(572.24-545.92)	5.2
	1/0.25	551.5	144.9	(533.68-562.88)	5
	1/4	538	182.85	(482.16-553.84)	4.2
	1/8	523	221.95	(487.92-543.04)	3.7
Dimethyl sulfoxide	Without polymer	576.8	121.56	(587.41-562.3)	6.3
	1/0.25	571	136.12	(555.13-585.36)	6
	1/4	552.1	161.54	(493.56-570.5)	5.1
	1/8	537.8	191.88	(505.13-558.2)	4

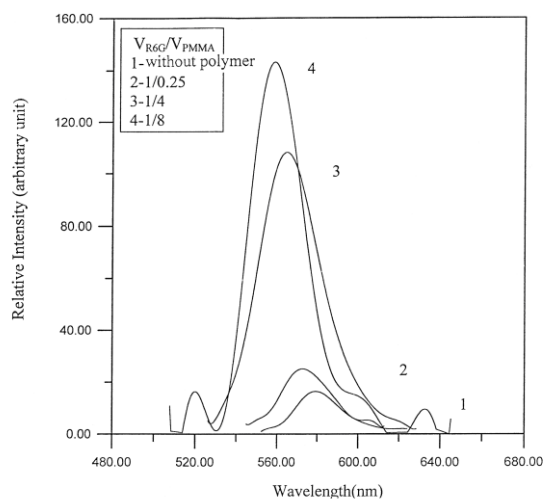

**Fig. (7B):-**The emission spectra of RhB in dimethyl sulfoxide of concentration 10-4M/l, with different volume proportions of polymer.

**Table 4: Spectro parameters of emission spectra of rhodamine 6G for concentration 10-4 M/l in chloroform , and, dimethyl sulfoxide with different volume proportions of polymer.**

Rhodamin 6G					
Solvent	$V_{RB}/V_{PMMA}$	$(nm)\lambda_{Flu.}$	$I_{(max.) Flu.}$	$\lambda_{Flu.}\Delta$ At FWHM (nm)	Quantum Yield ( $Q_{FM}$ )
Chloroform	Without polymer	574	26.45	(561.44-598.88)	0.11
	1/0.25	565.25	48.6	(549.52-582.32)	0.7
	1/4	558.5	133.2	(545.92-574.4)	0.78
	1/8	551.5	192.6	(537.28-567.2)	0.85
Dimethyl sulfoxide	Without polymer	580.8	16.16	(567.84-593.81)	0.5
	1/0.25	574	25.2	(560-589.89)	0.57
	1/4	565	110.6	(548.91-584.01)	0.18
	1/8	558	145.6	(544.01-575.68)	0.74

### References:

- Duarte. F. J., Hillman (Eds L. W.), (1990). Dye laser principles; Academic Press. , New York.
- Duarte. F. J., (1999). Photo Thermal Analysis of Polymeric Dye Laser Materials. Appl. Opt. 38: 6347.
- Duarte. F. J., Taylor. T. S., Costela. A., Garcia Moreno. I., Sastre. R., (1998). Temperature Insensitive Fiber-Optic Torque and Strain Sensor. Appl. Opt., 37: 18.
- Giffin. S. M, Haskell. W. J., Mckinnie. I. T., Woolhouse. A.K., Haskell. T.G., (1999). Fluorescence Quantum Yields of Rhodamine 6G and Fluorescein in Nine Solvent., J. Mod. Opt., 46: 1941.
- Zhang. Q. Y., Wang. L., Hu. L. L., Jiang. Z. H., (1999), Fluorescence Quantum Yields of Some Rhodamine Dyes, Chem. Phys. Lett., 16: 384,.
- Wu. S., Zhu. C., (1999). Highly Efficient Polymeric Dye Laser Pumped at 1.06  $\mu m$  . Opt. Mater, 12: 99.
- Rahn. M. D., King. T. A., Mod. J. (1998). Singlet Oxygen and Dye-Triplet State Quenching in Solid State Laser Consisting of Pyrromethan 567 Doped Poly. Opt., 45: 1259.
- Gvishi. R., Gonen. E., Kalisky.Y, Rotman. S., (1999). Solvent Dependence of The Fluorescence Lifetimes of Xanthene Dyes. Opt. Mater, 13: 129.
- Ahmad. M., Rahn. M. D., King. T. A., (1999), Photothermal Analysis of Polymeric Dye Laser Material Exited., Appl. Opt., 38: 6337.
- Reisfeld. R., (1972). Photoluminescence in ZnO-CdO-SiO<sub>2</sub>. NBS 76A: 613.
- Holzer. W., Gratz. H., Schmitt. T., Penzkofer. A., Costela. A., Garcia Moreno. I., Sastre. R., Duarte. F. J., (2000). Photo-Physical Characterization of Rhodamine 6G in a 2-Hydroxyethyl.methacrylate methyle-methacrylate Copolymer. Chem. Phys., 256:125.
- A. A. Alfhadawi; Luminescence Spectra for Two Dyes Rhodamine B, Rhodamine 6G in different Media, Msc. Thesis Baghdad University (2002).
- Foster. Th., and, Koing. E., Bunsenges. Bre., (1957). Relation Between Absorption Intensity and Fluorescence Lifetimes of molecules. Physik. Chem., 61: 344.
- Selwyn. J. E., and, Steinfeld. J. I., (1972). Absolute Quantum Efficiencies. J. Phys. Chem., 76: 762.

- 15-Rohatgi. K. K., and, Sinehal. G. S., (1966). Studies on The Aggregation of Dyes in Aqueo Solution. *J. Phys. Chem.*, 70: 1695.
- 16-Suzuki. K., and, Tsuchig. M., (1971). Fluorescence Efficiency of Laser Dyes. *Bull. Chem. Soc. Japan.*, 44: 967.
- 17-Gal. M. E., Kelly. G. R., and, Kurucscv. T., (1973). Fluorescence Excitation Spectrum of Organic Compounds in Solution. *J. Chem. Soc. Faraday*, 1169: 395.
- 18-Muto. J., (1976). Magneto-Optical Studies of Perylene Tetracarbyxylic Acid Dimid Thin Film. *J. Phys. Chem.*, 80: 1342.
- 19-Lopez Arbeloa. I., and, Ruizo JEDA. P., (1981). Molecular Forms of Rhodamine B. *Chem. Phys. Lett.*, 79: 2: 347.
- 20-Ferguson. J., and, Mau. A. W. H., (1972). Absorption Study of Acid-Base Equilibria of Dye Solutions. *Australian, J. Chem.*, 17: 543.
- 21- Ferguson. J., and, Mau. A. W. H., (1973). A molecular Thermometer Based on Long-Lived Emission Form Platinum Octaethyl Porphyrin . *Australian, j. Chem.*, 26: 1617.
- 22- Levshin. L. V., Slavnova. T. D., Yuzhakov. V. I., Zorov. N. B., and, Pashchenko. V. Z. P., (1974). Effect of The Concentration of Rhodamine 6G on The Optical properties of its Ethanol Solution . *Russian, J. Phys. Chem.*, 48, 46.
- 23- Sadkowski. P. J., and, Fleming. G. R., (1978). Photophysics of Acid and Base Forms of Rhodamine 6G. *Chem. Phys. Lett.*, 57, 526.
- 24- Lopez Arbeloa. T., Lopez Arbeloa. F., Lopez Arbeloa. I., Costela. A., Garcia-Moreno. I., Figuera. J. M., Amat. Guerri. F., (1997). Fluorescenceand Lasing Properties of Rhodamine Dyes. *J. Lum.* 75, 309.
- 25- Reisfeld. R., Zusman. R., Choen. Y., Eyal. M., (1988). The Spectroscopic Behaviour of Rhodamine 6G in polar and non-polar Solvents and in Thin Glass and PMMA Films. *Chem. Phys. Lett.*, 147, 142.
- 26- Amat-Guerr. F.i, Costela. A., Figuera. J. M, Florid. F., Sastre. R., (1993). Radiative and non-Radiative Transitions of Rhodamines in Deuterated Solvent *Chem. Phys.Lett.*, 209:352.
- 27- Linuma. F., Mikawa. H., Shiota. Y., (1981). Hydrogen Bond Effects on Radiationless Electronic Transitions in Xanthene Dyes. *Macromolecular*, 14, 1747.
- 28- Dubois. A., Canva. M., Brun. A., Chaput. F., Jeanpierre Boilot, (1996). Photostability of Dye Molecules Trapped in Solid Matrices. *Appl. Opt.*, 35, 3193.
- 29- Costela. A., Garica-Moreno. I., Figuera. J. M., Amat-Guerri. F., Mallavia. R., Sastre. R, (1996). Long-Pulse Narrow Linewidth Dispersive Solid-State Dye Oscillator. *J. Appl.Phys.*, 80, 3167.
- 30- Costela. A., Florido. F., Garica-Moreno. I., Duchowicz. R., Amat-Guerri. F., Figuera. J. M., Sastre. R., (1995). Photostability of novel copolymers Function-alized with Laser Dyes Based on modified Rhodamine 6G an 1.8-Naphthalimide. *Appl.Phys. B* 60, 383.

## دراسة الخصائص الفيزيائية الضوئية لصبغة رودامين 6G للمحاليل السائلة والصلدة

نذيرة عباس علي التميمي\* سلوان كمال جميل\* أحسان علي الفهداوي\*

\*جامعة بغداد / كلية العلوم / قسم الفيزياء/ بغداد/ عراق

## الخلاصة:

تضمن هذا البحث دراسة الخواص الفيزيائية الضوئية ( الأمتصاص, التآلق, والناتج الكمي وزمن العمر) للمحاليل السائلة والصلدة لصبغة رودامين 6G. حيث تضمنت المحاليل السائلة التراكيز المختلفة للمذيبات الكلوروفورم, الميثانول وثنائي مثيل أوكسيد الكبريت, أما المحاليل الصلدة فهي تتضمن مزج نسبة حجمية ثابتة من المحلول المركز للصبغة ( $1 \times 10^{-4}$  mole/liter) مع نسب حجمية مختلفة من المحلول المركز للبوليمر في الكلوروفورم وثنائي مثيل أوكسيد الكبريت.

أظهرت النتائج أن إضافة البوليمر الى المحاليل المركزة السائلة ( $1 \times 10^{-4}$  mole/liter) لصبغة رودامين 6G من المتوقع أن تؤدي الى تحسين الوسط الفعال لليزر الصبغة عند التراكيز العالية حيث تزداد ازاحة الأطياف باتجاه الطاقات العالية كما يزداد الناتج الكمي للتآلق ويقل زمن العمر الأشعاعي نسبيا.