

Modification and Study Biological Activity of Chitosan with Compounds Containing Azo Group

Ruwaidah S. Saeed * , Huda A. Hassan , Dheefaf F. Hassan , Muna S. Al-rawi 

Department of Chemistry, College of Education for Pure Science Ibn Al-Haitham, University of Baghdad, Iraq.
*Corresponding Author.

Received 11/09/2023, Revised 26/12/2023, Accepted 28/12/2023, Published Online First 20/08/2024



© 2022 The Author(s). Published by College of Science for Women, University of Baghdad.

This is an open access article distributed under the terms of the [Creative Commons Attribution 4.0 International License](https://creativecommons.org/licenses/by/4.0/), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract

In the present research synthesis and study of biological activity a series of new polymers modified of chitosan with compounds containing azo group. Beginning diazonium salt produced from 3,3'-dimethyl-[1,1'-biphenyl]-4,4'-diamine reacted with concentrated HCl acid and sodium nitrite. The coupling reaction between diazonium salt with substituted aromatic aldehyde to produce Azo derivatives (1-6). Azo Schiff bases Chitosan (7-12) were synthesized by condensation of Chitosan with Azo derivatives (1-6) in ethanol with some drops of glacial acetic acid. The structural modifications of Chitosan ring (linked to a bioactive azo moiety) were expected to give new derivatives (7-12) with a diverse range of biological functions. These compounds' structures have been determined using FT-IR, ¹H-NMR spectroscopic and Field Emission Scanning Electron Microscopy studies. Additionally, two other kinds of bacteria: *Staphylococcus aureus* and *E. coli* were tested for possible antibacterial properties utilizing some new compounds. Modified Chitosan (7-10) showed high activity comparable to a penicillin (used as the reference antibiotic), Especially the modified polymer(7), which showed high inhibition against both types of bacteria. The anticancer activity of modified chitosan (7) against MCF-7 (human breast carcinoma cells) using 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) assay was employed to determine and compare with normal cells WRL-68(the human hepatic cell line). Polymer (7) exhibited a high cancer cell inhibition rate and less toxicity to normal cells.

Keywords: Azo compounds, Chitosan, Diazonium salt, FESEM study, MCF-7, Schiff bases.

Introduction

Azo compounds are very important organic compounds having a wide spectrum of biological activities. Diazonium coupling reactions are typical electrophilic aromatic substitutions in which the positively charged diazonium ion in the electrophile interact with the electron-rich ring of substituted benzaldehyde^{1,2}.

Schiff bases, having imine groups (C=N) are formed by nucleophile addition (condensation reaction of (NH₂) primary amines with carbonyl groups (C=O) of aldehydes or ketones. These compounds have been used for industrial purposes such as pigments,

catalysts, liquid-liquid extraction, active transport, intermediates in organic synthesis and as polymer stabilizers³⁻⁶. Azo compounds, such as the azobisisobutyronitrile (AIBN) may be utilized as radical initiators in the polymerization of the alkenes for making plastics⁷. The aromatic azo compounds have been utilized as acid-base indicators like the methyl orange, methyl red and Congo red⁸. Chitosan is a natural biopolymer generated from the parent substance chitin, It is a semi-crystalline, linear, nontoxic, biocompatible, biodegradable, odorless, safe and antibacterial polymer^{9,10}. Due to its ability

to produce bio functional materials, it has a wide range of biological activities including anti-diabetic, anti-oxidant, anti-bacterial activities, antimicrobial, antitumor and is used pharmaceutically as an anticoagulant agent¹¹⁻¹³. It can also be helpful in several fields including textiles, environmental protection, water treatment, cosmetics and biotechnology. Due to the presence of -OH and NH₂ groups, which separate chitosan from cellulose, its structure is easily changed to produce various derivatives¹⁴⁻¹⁶. The modified chitosan exhibits new properties like biological activity and biocompatibility¹⁷⁻¹⁹. Because of all the above datum

facts, This study is aimed at the achievement of the syntheses, characterization and study of the biological activities of some synthesized new polymers modified of chitosan based to Schiff bases containing azo groups, whose molecules include the three moieties, chitosan, imine group (-N=CH-) and azo groups together²⁰, since the combination of all these biologically active moieties in one molecule may increase the likelihood of producing more potent newly-developed prodrugs with a wide range of diverse biological activities (antibacterial and anticancer), as an attempt to correlate the biological results with their structural characteristics.

Materials and Methods

All chemicals have been supplied from CDH, SCR and BDH. The FT-IR Spectra have been registered on Shimadzu FT-IR-8400 s, ranging between 400-4000cm⁻¹, using the potassium bromide disk. Company: Ultra Shield 400MHz, Bruker, University of Basrah, Iraq performed the ¹H-NMR spectra. With DMSO serving as the solvent, TMS has been used as the internal standard. Iranian University of Tehran performed FESEM. At the Central Environmental Laboratory of the University of Baghdad's College of Science, biological activity was conducted. The Department of Molecular and Medical Biotechnology at AL-Nahrain University's Biotechnology Research Center conducted anticancer screening.

Synthesis of Azo compounds (1-6)

3,3'-Dimethylbiphenyl-4,4'-diamine (2.12g, 0.01mole) has been dissolved in 2mL of the 2N hydrochloric acid and 20mL of the distilled water. This solution has been cold at 0-3 °C in an ice-water bath. Sodium nitrite (1.38g, 0.02mole) has been dissolved in 10mL of the distilled water and added dropwise to a cold solution while stirring. The mixture (diazonium solution) is stable for a few minutes. The above cold diazonium solution was added slowly to a well stirred solution to 0.02 mole from different substituted benzaldehydes: (2.98g.) of N,N-dimethylbenzaldehyde, or (2.81g.) of 2-chlorobenzaldehyde, or (2.44gm) of 4-hydroxybenzaldehyde, or (3.13g.) of 5-chloro-2-hydroxybenzaldehyde, or (3.04g.) of 2-hydroxy-3-methoxybenzaldehyde or (3g.) of 4-Ethoxybenzaldehyde) in 20mL of absolute ethanol and 5mL of 10% sodium hydroxide and the

mixture was cooled to a temperature of 0-5 °C with stirring for 2hrs in order to obtain coupling agent. The progress of the reaction was monitored by TLC. When the reaction was completed, the orange to red compound result was precipitated, then filtered and recrystallized from absolute ethanol^{21,22}. Physical properties of compounds(1-6) are listed in Table .1

Synthesis of Azo Schiff bases Chitosan (7-12)

A mixture of ethanol (10 mL) and glacial acetic acid (5 mL) was added to chitosan (0.5 g.), which was then dissolved and stirred for 30 minutes at room temperature, then add one of azo derivatives(1-6) (0.01mol). The mixture was heated by stirring for 24 hours in a water bath at a 60°C. The reaction mixture was cooled, and the residue produced was filtered, washed with EtOH, dried at room temperature for 24 hours²³

Biological Activity :

Antibacterial Activity

Some of the synthesized compounds and modified polymers have been screened for antibacterial activities against (*Staphylococcus* and *Escherichia coli*) using cup-plate agar diffusion method²⁴. Penicillin (50µg/ml) was used as a standard drug for antibacterial activity. These sterilized agar media were poured into petri dishes and allowed to solidify. Some of the synthesized compounds (50µg/ml) were placed serially in the cavities with the help of a micropipette and allowed to diffuse for 1 hr. DMSO was used as a solvent for all the compounds and as a control. These plates were incubated at 37°C for 24 hr for antibacterial activities. The zone of inhibition observed around the cups after respective incubation was measured in mm.

Anticancer Activity^{25,26}


The cytotoxic effect of modified chitosan (7) against MCF-7 (human breast carcinoma cells) was studied and compared with normal cell line WRL-68 (the human hepatic cell line). The anti-proliferative activity of modified polymer (7) was tested by studying their ability to inhibit the proliferation of human breast carcinoma cells (MCF-7). The MTT test was used in 96-well plates to investigate the cytotoxic impact of polymer (7). Cells were treated

with polymer (7) after 24 hours or when a confluent monolayer was established. After 24 hours of treatment, cell viability was determined by removing the medium, μl /well solutions of MTT and incubating for 4 hr. at 37°C . The crystals in the wells were solubilized after the MTT solution was removed by adding 200 μL of DMSO (Dimethyl Sulphoxide) and incubated at 37°C for 15 minutes while shaking. with the use of a microplate reader, the absorbency was determined at 620 nm.

Results and Discussion

Azo aldehyde derivatives (1-6), Scheme.1 were obtained by coupling reaction between diazonium salt with two moles of substituted aldehydes. The

new compounds (1-6) were identified by FTIR and $^1\text{H-NMR}$ spectroscopy obtained for elegant compounds are listed in Tables 2 & 4 respectively.

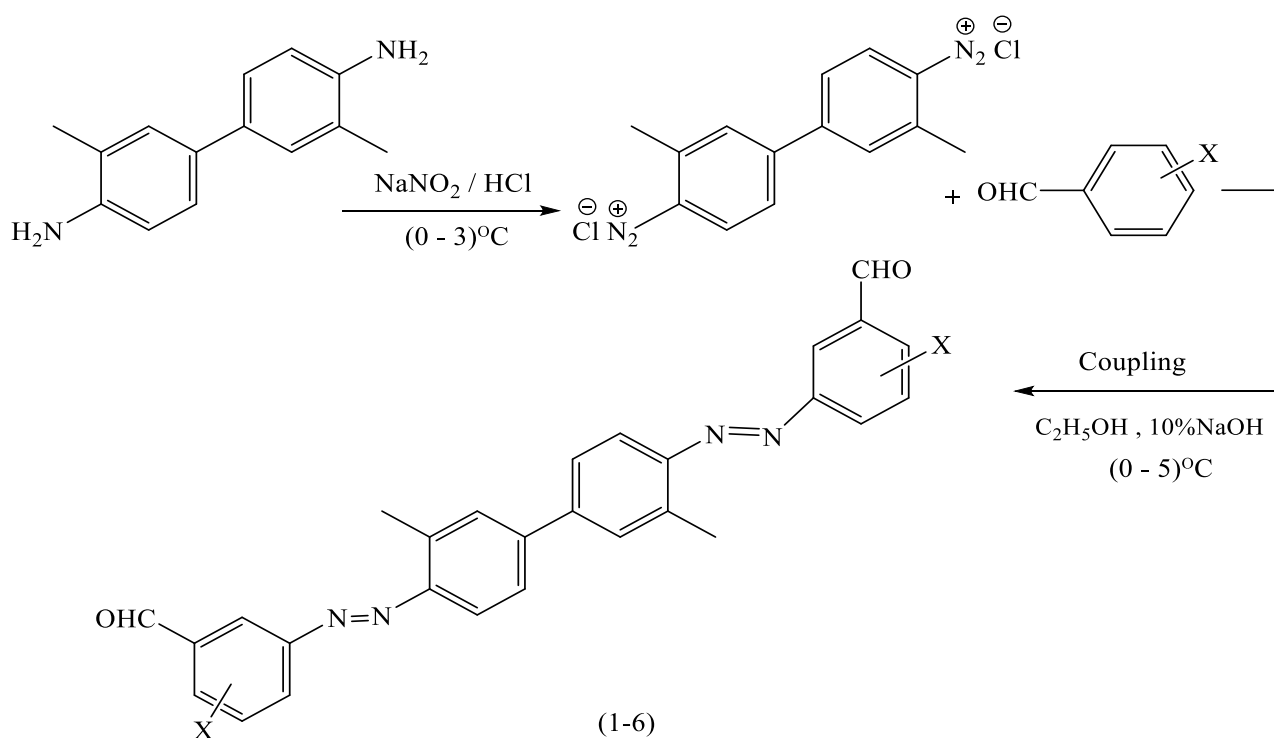


X = 4-N(CH₃)₂, 2-Cl, 4-OH, 5-Cl-2-OH, 2-OH-3-OCH₃, 4-OCH₂CH₃

Scheme1. Synthesis of compounds (1-6)

Azo Schiff bases chitosan (7-12) were produced from chitosan reaction with azo derivatives (1-6). The novel polymers modified of chitosan Scheme 2, were identified by FTIR and $^1\text{H-NMR}$ spectroscopy²³.

The FT-IR spectral data are given in Table 3. $^1\text{H-NMR}$ spectra are listed in Table 4.




These findings provide good support for the formation of the structure for polymers of chitosan.

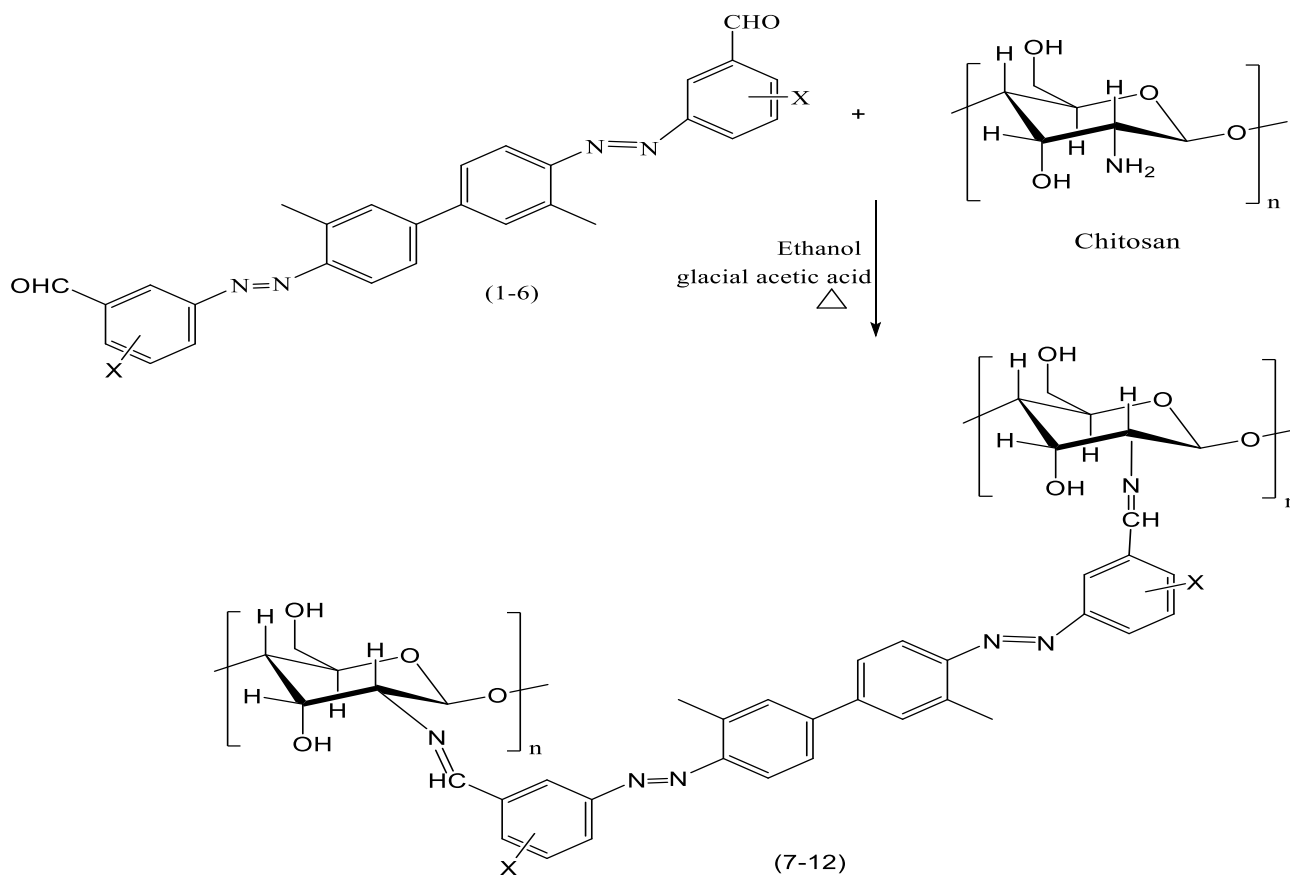

X = 4-N(CH₃)₂, 2-Cl, 4-OH, 5-Cl-2-OH, 2-OH-3-OCH₃, 4-OCH₂CH₃

Scheme2. Synthesis of Azo Schiff Bases Chitosan (7-12)

Table 1. Physical properties of compounds (1-6)

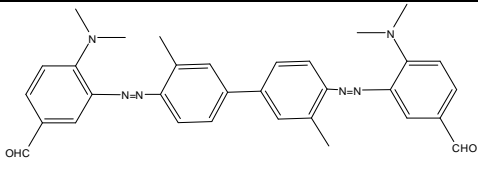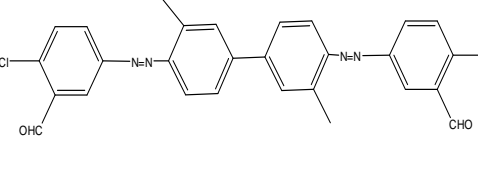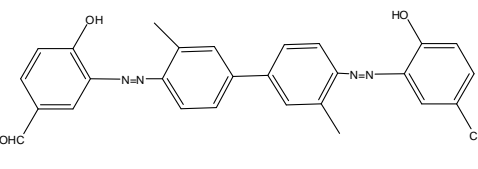Com. No.	Nomenclature	Structural formula	M.P. °C	Yield %	Colour
1	3,3'-(3,3'-dimethyl biphenyl-4,4'-diyl) bis(diazene-2,1-diyl) bis(4-(dimethylamino) benzaldehyde)		63-65	79	Orange
2	5,5'-(3,3'-dimethyl biphenyl-4,4'-diyl) bis(diazene-2,1-diyl) bis(2-chloro-benzaldehyde)		265-267	76	Red Brown
3	3,3'-(3,3'-dimethyl-biphenyl-4,4'-diyl) bis (diazene-2,1-diyl) bis(4-hydroxy-benzaldehyde)		273-275	87	Pale red

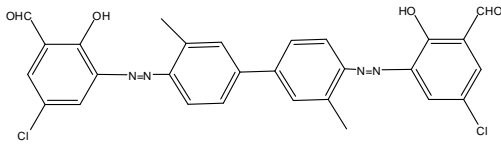
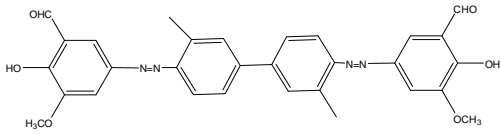
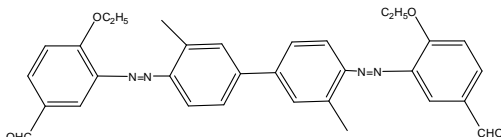
4	3,3'-(3,3'-dimethyl biphenyl-4,4'-diyl)bis (diazene-2,1-diyl)bis(5-chloro-2-hydroxy benzaldehyde)		288-290	89	Brown
5	5,5'-(3,3'-dimethyl biphenyl-4,4'-diyl)bis (diazene-2,1-diyl)bis(2-hydroxy-3-methoxy benzaldehyde)		>300	90	Red Brown
6	3,3'-(3,3'-dimethyl biphenyl-4,4'-diyl)bis (diazene-2,1-diyl)bis(4-ethoxy-benzaldehyde)		>300	76	Dark orange

Table 2. FT-IR spectroscopy data of compounds (1-6)

Com. No.	(C-H) arom cm ⁻¹	(C-H) aliph cm ⁻¹	(C-H) aldehyde cm ⁻¹	(C=O) cm ⁻¹	(N=N) cm ⁻¹	(C=C) cm ⁻¹
(1)	3024	2912,2883	2819,2731	1662	1550,1535	1597,1575
(2)	3086	2912,2890	2800,2750	1674	1566,1530	1585,1570
(3)	3024	2954,2899	2810,2762	1647	1559,1539	1600,1580
(4)	3051	2908,2885	2828,2798	1664	1552,1533	1600,1580
(5)	3050	2920,2886	2822,2738	1681	1573,1537	1600,1565
(6)	3024	2920,2892	2870,2762	1660	1560,1525	1600,1575

Table 3. FT-IR data of modified chitosan (7-12)

Com. No.	(O-H) and (N-H) cm ⁻¹	(C-H) aliph. cm ⁻¹	(C=N) cm ⁻¹	(C=C) cm ⁻¹	(N=N) cm ⁻¹
(7)	3402	2916, 2890	1648	1600,1589	1523
(8)	3410	2924,2887	1630	1604,1578	1550
(9)	3448	2943,2880	1641	1584,1500	1564
(10)	3411	2910,2895	1630	1597,1500	1556
(11)	3421	2924,2893	1635	1600,1587	1558
(12)	3414	2947,2896	1620	1602,1580	1554

Table 4. ¹H-NMR spectral data (ppm) for some compounds

Com. No.	Spectral signals in ¹ H-NMR (δ, ppm) (in DMSO-d ₆)
(1)	2.18 (s, 6H, CH ₃), 3.46 (s, 12H, N(CH ₃) ₂), 6.77-7.69 (m, 12H, Ar-H), 9.67 (s, 2H, CHO).
(2)	3.83(s, 6H, CH ₃), 7.05-7.83 (m, 12H, Ar-H), 8.64(s, 2H, CHO).
(6)	1.31-1.37(t, 6H, OCH ₂ CH ₃), 4.12-4.17 (q, 4H, OCH ₂ CH ₃), 3.35 (s, 6H, CH ₃), 7.10-7.87 (m, 12H, ArH), 9.86 (s, 2H, CHO)

Anti-bacterial activities of some of the synthesized compounds and modified chitosan (azo schiff bases chitosan) were observed (*in vitro*) against *E. coli* (G-) and (G+) *Staphylococcus aureus*, based upon agar diffusion approach. A standard drug (50μg/mL of Penicillin) has been utilized for comparison with synthesized azo compounds and modified chitosan. The results showed that modified chitosan (7-10) has a higher effectiveness than azo compounds (1-4). The reason for the increased effectiveness is the presence of chitosan (biopolymer), which has biological activity against bacteria because it contains amino groups with positive charges that bind with the negative charges present on the surface

Antibacterial Activity²⁷⁻²⁹

of the bacterial cell, which causes a change in its properties. Such as the permeability of its cell membrane and an imbalance in osmosis processes, which results in preventing the growth of bacteria, Figs. 1, 2. All of the compounds and their antibacterial activities have been listed in Table 5.

Table 5. zone of inhibition (in mm) of some synthesized azo compounds (1-4) and modified chitosan (7-10) .

Com. No.	<i>Escheria .coli</i>	<i>Staphylococcus aureus</i>
Penicillin	22	22
(1)	15	16
(2)	10	9
(3)	9	9
(4)	10	12
(7)	26	30
(8)	23	24
(9)	25	21
(10)	25	29

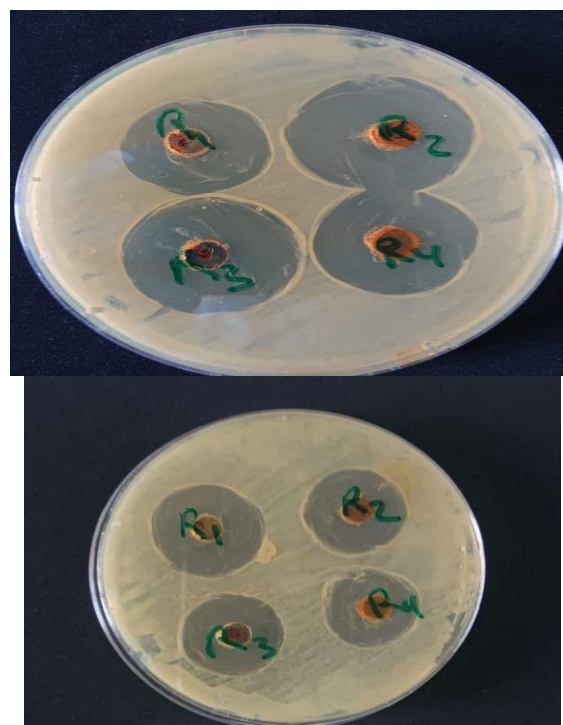


Figure 2. Antibacterial activities of modified chitosan (7-10)

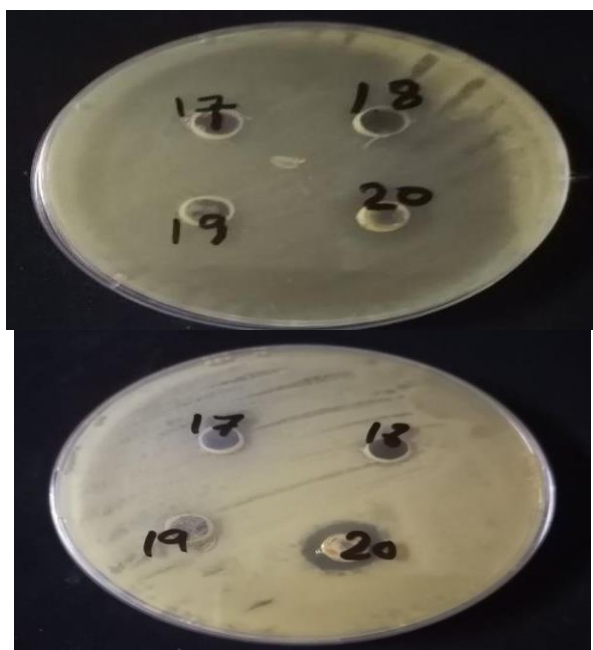
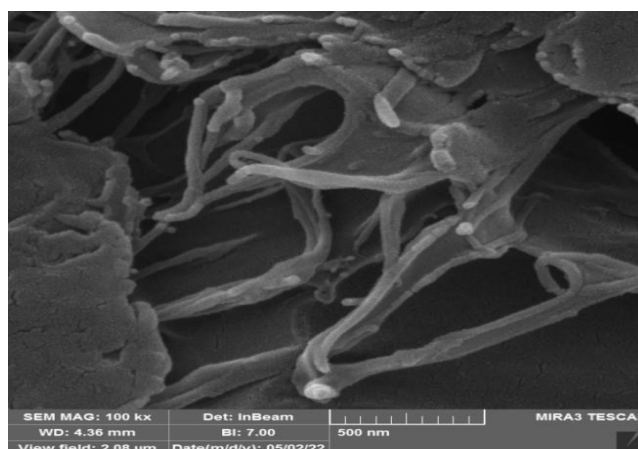


Figure 1. Antibacterial activities of azo compounds (1-4)

FESEM Studies ³⁰⁻³⁴

FESEM micrographs have been utilized to study changes in surface morphology for prepared polymers(7) and (12). Figs. 3,4 shows the modified chitosan's surface morphology. In FESEM images, it can be noticed increasing average size of the pores in comparison with chitosan pore size. Variations of surface morphology result from new bonds in the polymer that have been prepared.



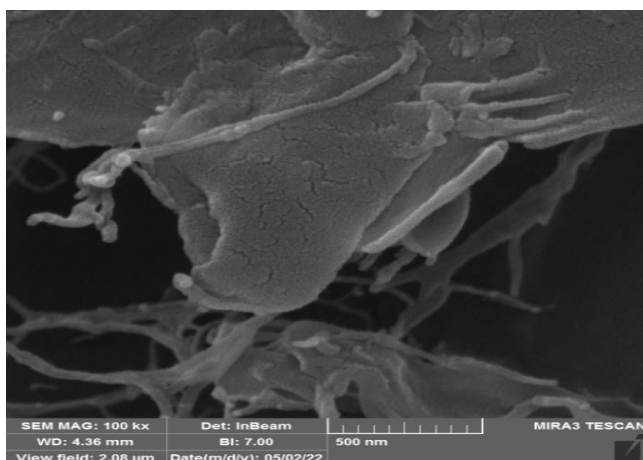


Figure 3. FESEM of modified chitosan (7)

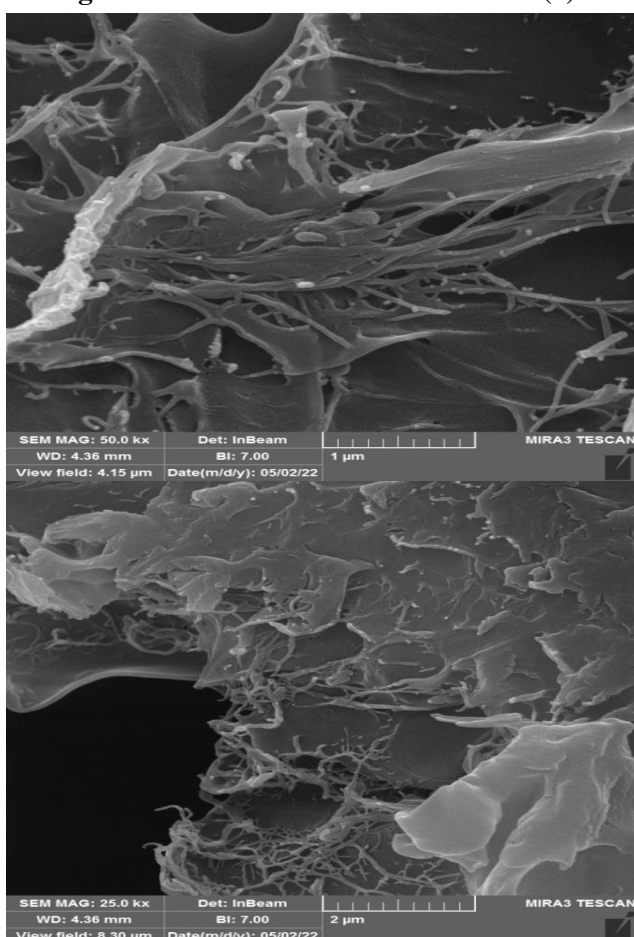


Figure 4. FESEM of modified chitosan (12)

Anticancer Activity³⁵⁻³⁸:

The results demonstrated the ability of prepared modified chitosan to destroy and kill cancer cells as shown in Figs.5-7. Table 6 shows the inhibition ratio of the modified polymer(7) equal is 84.65 while table 7 shows cell viability% is 15.35. Table 8 show the activity of polymer(7) against cancer cells is dependent on concentration ,the inhibition rate at

the concentration (10, 25, 50, 75, 100) µg \ ml equal (25.31, 40.45, 63.72 80.40, 84.65) respectively and IC50 of polymer(7) in table 9 equal 33.26 with MCF-7 and 83.33 with WRL-68 .

Chitosan or its derivatives selectively penetrate tumor cells and exhibit anti proliferative activities via antiangiogenic, immunoenhancing, antioxidant defense, apoptosis and enzymatic regulation possibly because azo molecules are involved in the inhibition of DNA, RNA and protein synthesis, as well as hindering carcinogenesis. In addition, the presence of (N=N) in the azo molecular structure is accountable for the interaction with the active site of the target protein

Table 6. The inhibition of cells growth of polymer (7) µL/well

Concentration µg mL ⁻¹	Inhibition of cells growth for MCF-7
10	25.31
25	40.45
50	63.72
75	80.40
100	84.65

Table 7. Differences between different treatments at concentration levels within MCF-7and WRL cell line

Conc. µg/MI	MCF-7		WRL-68	
	Mean Viability%	SD	Mean Viability%	SD
10	74.69	1.26	96.95	1.14
25	59.56	0.94	91.85	3.85
50	36.28	2.67	91.80	2.01
75	19.60	2.43	78.03	6.36
100	15.35	2.47	67.91	5.61

Table 8. Differences between MCF-7andWRL with respect to treatments

multiple comparisons test	Below threshold	Summary	Adjusted P Value
MCF-7 - WRL-68			
10	Yes	**	<0.0001
25	Yes	**	<0.0001
50	Yes	**	<0.0001
75	Yes	**	<0.0001
100	Yes	**	<0.0001

Table 9. IC50 of polymer (7)

Cell Line	IC ₅₀ µg mL ⁻¹
MCF-7	33.26
WRL-68	83.33

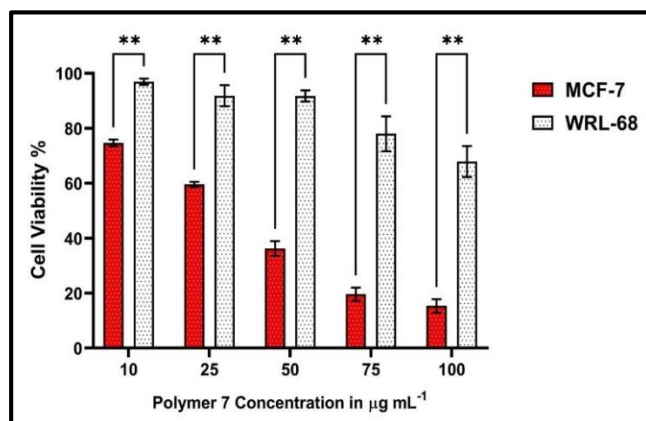


Figure 5. Cell Viability of polymer (7) on MCF-7 and compare with WRL-68

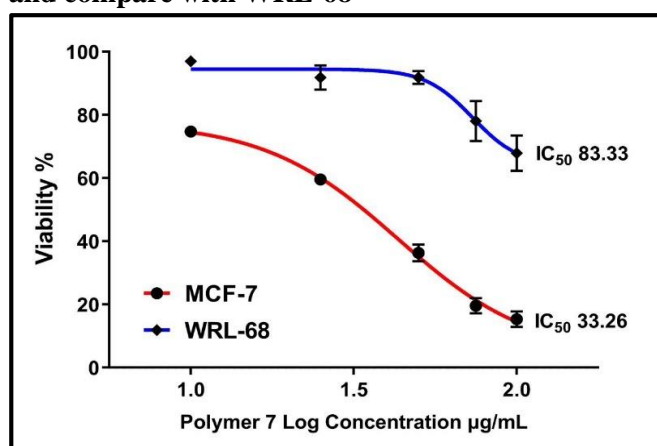


Figure 6. IC₅₀ of polymer (7) on MCF-7 and compare with WRL-68.

Conclusion

In this study, synthesis, characterization and study of antibacterial/ anticancer activities of some new modified polymers containing chitosan and azo group. FESEM studies showed the changes in the surface morphology of the synthesized polymers due to the new bonds between Chitosan and azo compounds. Results have shown that polymers had a greater diameter of the growth inhibition zone, polymer (7) had shown quite good inhibition towards the *Staphylococcus aureus* and *E. coli*. Anti-bacterial characteristics of the chitosan are associated with its poly-cationic character and the modified chitosan (7-

Acknowledgment

We appreciate the cooperation of the teaching staff in the Department of Chemistry in the College of

Authors' Declaration

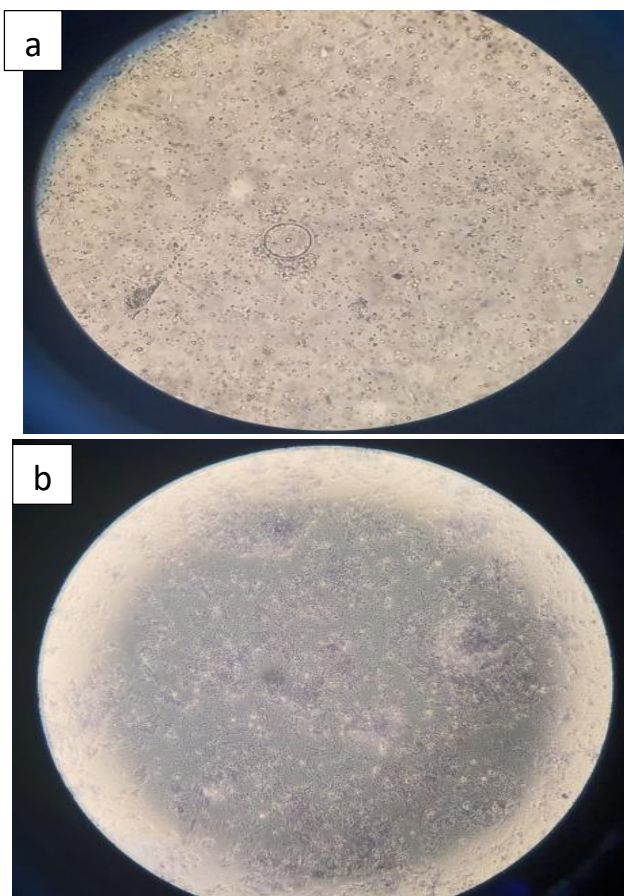


Figure 7. (a) Image of the MCF-7 well before staining (b) Image of the MCF-7 well after Staining

10) has a higher effectiveness than azo compounds (1-4) due to the presence of the chitosan (biopolymer). The protonated functional groups of the chitosan interact with the negative-charged membranes of the cells of the micro-organisms, which cause damage. Finally, studied the anticancer activity of modified chitosan (7) against MCF-7 (human breast carcinoma cells) and compare with normal cells WRL-68 (the human hepatic cell line). Polymer (7) exhibited high Inhibition rate and less toxicity with IC₅₀ = 33.26 on MCF-7 and 83.33 on WRL-68 cancer cell lines.

Education for Pure Science Ibn Al-Haitham, University of Baghdad.

- Conflicts of Interest: None.
- We hereby confirm that all the Figures and Tables in the manuscript are mine ours. Besides, the Figures and images, which are not mine ours, have been given permission for re-publication attached to the manuscript.
- Authors sign on ethical consideration's approval.
- Ethical Clearance: The project was approved by the local ethical committee at the University of Baghdad.
- No animal studies are present in the manuscript.
- No potentially identified images or data are present in the manuscript.

Authors' Contribution Statement

R.S. S. has designed the work plan, analyzed the results, wrote the article and reviewed the article. H.

A. H., D. F. H. and M. S. A. participated in the practical part and conducted the analyzes.

References

1. Abdel Tawab MS, Shaikha SA, Ibrahim MA, Anticancer activity of novel Schiff bases and azo dyes derived from 3-amino-4-hydroxy-2H-pyrano[3,2-c]quinoline-2,5(6H)-dione, Heterocycl Commun. 2020; 26(1): 192-205. <http://dx.doi.org/10.1515/hc-2020-0116>
2. Al Zoubi W, Al-Hamdani A AS, Young G K, Schiff bases and their complexes: Recent progress in thermal analysis, Sep Sci Technol. 2017; 52 (6): 1052-1069. <https://doi.org/10.1080/01496395.2016.1267756>
3. Marwa AD, Amer JJ. Synthesis, characterization and biological evaluation of thiazolylazo ligand complexes with some metal ions. J Phys Conf. 2020; 1664 :1-18. <http://dx.doi.org/10.1088/1742-6596/1664/1/012090>
4. Al Zoubi W, Al-Hamdani A AS, Ahmed S D, Ko Y Gun, A new azo-Schiff base: Synthesis, characterization, biological activity and theoretical studies of its complexes. App Organomet Chem. 2018; 32 (1): 3574. <https://doi.org/10.1002/aoc.3895>
5. Lekha L, Raja K K, Rajagopal G, Easwaramoorthy D. Synthesis, spectroscopic characterization and antibacterial studies of lanthanide (III) Schiff base complexes containing N, O donor atoms. J Mol Struct. 2014; 1056: 307-313. <http://dx.doi.org/10.1016%2Fj.molstruc.2013.10.014>
6. Kamoon R A, Al-Mudhafar M M J, Omar T N A. Synthesis, Characterization and Antimicrobial Evaluation of New Azo Compounds Derived from Sulfonamides and Isatin Schiff Base. Int J Drug Deliv Technol. 2020; 10 (1): 150-155.
7. Sallal Z A , Ghanem H T, Synthesis and Identification of New Oxazepine Derivatives bearing Azo group in their structures, Iraqi J Sci. 2018; 59(1A): 1-8. <http://dx.doi.org/10.24996/ij.s.2018.59.1A.1>
8. Carey F A. Important azo compound In: Organic Chemistry. 7th ed, 2008; New York.
9. Ali A T , Abdul Karem L K, Biosynthesis, Characterization, Adsorption and Antimicrobial studies of Manganese oxide Nanoparticles Using Punica Granatum Extract, Baghdad Sci .J .2024;21(3) <https://doi.org/10.21123/bsj.2023.8183>
10. Jessica C, Domenico I, Alessia C, Francesca C, Rosamaria L, Maria Stefania S. A Review on the Antimicrobial Activity of Schiff Bases: Data Collection and Recent Studies. Antibiotics. 2022; 11(2):191 <https://doi.org/10.3390/antibiotics11020191>
11. Jamka Z N , Mohammed W T . Assessment of the Feasibility of Modified Chitosan Beads for the Adsorption of Nitrate from an Aqueous Solution. J Ecol Eng. 2023, 24(2): 265–278, <https://doi.org/10.12911/22998993/156886>
12. Desislava S, Daniela A, Daniela A, Petar G, Ivanka N and Ivo G, Antimicrobial Properties of Chitosan-Modified Cotton Fabric Treated with Aldehydes and Zinc Oxide Particles. Mater. 2023; 16(14): 5090 <https://doi.org/10.3390/ma16145090>
13. Natalia D, Alexey L, Balzhima S, Alla I, Valery V, New N-Methylimidazole-Functionalized Chitosan Derivatives: Hemo compatibility and Antibacterial Properties. Biomimetics 2023, 8(3): 302. <https://doi.org/10.3390/biomimetics8030302>
14. Paula S, Ana P L D, Giovanna M, Declan M D, Janaina S C, Marcelo G, Synthesis and Characterization of Silver Nanoparticles for the Preparation of Chitosan Pellets and Their Application in Industrial Wastewater Disinfection. Water. 2023; 15(1): 190. <https://doi.org/10.3390/w15010190>
15. Danmin Y, Qun L, Yahui G, Shoumei W, Fanrong M, Wuyin W, et.al. Characterization of silver nanoparticles loaded chitosan/polyvinyl alcohol antibacterial films for food packaging. Food Hydrocoll. 2023; 136. Part B: 108305. <https://doi.org/10.1016/j.foodhyd.2022.108305>
16. Olivia H R, Samy S, Hussein M, Abdel-Gawada O F, Elzanatya A M, et al. Synthesis, Characterization and Biological Activity of Schiff Bases Based on Chitosan and Acetophenone Derivatives. Adv J Chem A. 2020; 3(3): 274-282. <https://doi.org/10.33945/SAMI/AJCA.2020.3.5>

17. Al-Harby N F, Albahly E F, Mohamed N A, Synthesis and Characterization of Novel Uracil-Modified Chitosan as a Promising Adsorbent for Efficient Removal of Congo Red Dye. *Polym.* 2022; 14 (2): 271. <https://doi.org/10.3390/polym14020271>
18. Loc N X, Tuyen P T T, Mai L C, Do Thi My Phuong, Chitosan-Modified Biochar and Unmodified Biochar for Methyl Orange: Adsorption Characteristics and Mechanism Exploration. *Toxics.* 2022; 10 (9): 500. <https://doi.org/10.3390/toxics10090500>
19. Shlaka W A, Saeed RS. Gold and Silver Nanoparticles with Modified Chitosan /PVA : Synthesis, Study The Toxicity and Anticancer Activity. *Nanomed Res J.* 2023; 8(3): 231-245. <https://doi.org/10.22034/nmrj.2023.03.002>
20. Kokila T, Chaitany J R, Vanaraj R, Selvakumari U, Madhappan S, Vinit R, et al. Update on Chitosan-Based Hydrogels: Preparation, Characterization, and Its Antimicrobial and Antibiofilm Applications. *Gels.* 2023; 9(1): 35. <https://doi.org/10.3390/gels9010035>
21. Ibraheem H H, Abood N K, Salim A J. Synthesis and characterize new heterocyclic compounds derivatives from diazonium salt derivatives. *wjpls,* 2016; 2(4): 353-361.
22. Hasan A M., Sura M. Abdul Majeed., Detection of Anti-cancer Activity of Silver Nanoparticles Synthesized using Aqueous Mushroom Extract of *Pleurotus ostreatus* on MCF-7 Human Breast Cancer Cell Line. *Iraqi J. Sci.* 2024;65(4) : 1886-1894. <https://doi.org/10.24996/ijs.2024.65.4.9>
23. El-Gharably A. A., El-Refaie S. Kenawy, Ahmed A. Safaan, Saad A. Aboamna, Yehia A.-G. Mahmoud, Hamada S. A. Mandour, J. *Polym. Res.,* 2022; 29: 141. <https://doi.org/10.1007/s10965-021-02672-1>
24. Sanaa A. AL sahib and Sana Hitur awad, Synthesis, Characterization of Chitosan para- hydroxyl Benzaldehyde Schiff Base Linked Maleic Anhydride and the Evaluation of Its Antimicrobial Activities, *Baghdad Sci J.* 2022;19 (6) :1265-1275 <http://dx.doi.org/10.21123/bsj.2022.5655>
25. Israa Abd Alhassan Hamdan and Jumbad Tomma Synthesis and Biological Activity of Some New 1,3,4-Oxadiazoles Derived from Carboxylic Acids, *Russ. J. Org. Chem.,*2024; 60(1):164-172 . <http://dx.doi.org/10.1134/S1070428024010214>
26. Rasheed H A M, Al-Majidi S. M. H., Synthesis, Molecular Docking Study, Anti-Oxidant and Cytotoxicity Evaluation of New Spiro Six Membered Ring Derivatives of 5-nitro isatin, *Iraqi J Pharm Sci,* 2024 ;33(2):36-48 <https://doi.org/10.31351/vol33iss2pp36-48>
27. Muslim R F, Majeed I Y, Saleh S E, Owaid M N, Abbas J A, Preparation, Characterization and Antibacterial Activity of some New Oxazolidin-5-one Derivatives Derived from Imine Compounds. *J Chem Health Risks* 2022; 12(4): 725-732. <https://doi.org/10.22034/jchr.2022.688557>
28. Saeed R S, Matty F S, Samir A H, Al-Rawi M S. Synthesis, Characterization and Antibacterial Study of Selected Metal Complexes Derived from Modified of PVA. *J Glob Pharma Technol.* 2019; 11(2): 108-117.
29. Tomma J H, Al-Obaidi O B, Al-Dujaili A H, A new thiazolidinone and triazole derivatives: Synthesis, characterization and liquid crystalline properties. *J Mol Struct.* 2022; 1270: 133817 <http://dx.doi.org/10.1016/j.molstruc.2022.133817>
30. Marwa M. Salih, Khawla H. Zghair, The Cytotoxic Effect of ZnO Nps Against the Intracellular Amastigotes of *Leishmania Donovanii* in Vitro. *Iraqi Journal of Science,* 2017; 58(4C) : 2285-2290, <https://doi.org/10.24996/ijs.2017.58.4C.3>
31. Taha A A, Hameed N J, Rashid F H, Decolorization of Phenol Red Dye by Immobilized Laccase in Chitosan Beads Using Laccase -Mediator -System Model. *Baghdad Sci J.* 2020; 17(3): 720-725. <https://doi.org/10.21123/bsj.2020.17.3.0720>
32. Hassan H A., Saeed R S, Hassan D F., Al-rawi M S., Synthesis and Evaluation Biological Activity of Some New Polymers Derived From 3,3'-dimethoxybiphenyl-4,4'-diamine, *J Nanostruct.* 2023;13(3): 854-862. <https://doi.org/10.22052/JNS.2023.03.026>
33. Alesa H J, Aldabbag B M, Salih R M. Natural Pigment -Poly Vinyl Alcohol Nano composites Thin Films for Solar Cell. *Baghdad Sci J.* 2020; 17(3): 832-840. <https://doi.org/10.21123/bsj.2020.17.3.0832>
34. Saeed R S, Attiya H G, Obead K A. Synthesis and Characterization of Grafted Chitosan Blending with Polyvinyl alcohol / Nanocomposite and Study Biological Activity. *Baghdad Sci J.* 2023; 20(5): 1692-1700. <https://doi.org/10.21123/bsj.2023.7574>
35. Al-Ziaydi A G, Al-Shammari A M, Hamzah M I, Kadhim H S and Jabir M S, Newcastle disease virus suppress glycolysis pathway and induce breast cancer cells death. *Virus Disease.* 2020; 31: 341-348. <https://doi.org/10.1007/s13337-020-00612-z>
36. Baker F. Abdallaha, Maha A. Younus, Ibraheem J. Ibraheem, Preparation, Characterization, Antimicrobial and Antitumor Activity of Chitosan Schiff base / PVA / PVP Au, Ag Nanocomposite in Treatment of Breast Cancer Cell Line, *Nanomed. Res. J.* 2021;6(4): 369-384 <https://doi.org/10.22034/nmrj.2021.04.007>
37. Freshney RI "Culture of Animal Cells: A manual of Basic Technique and Specialized Applications," 6th Edition, Wiley: New York, 2010.
38. Gao S, Ya BP, Dong WG, Luo HS. Ant proliferative effect of octreotide on gastric cancer cells mediated by inhibition of Akt/PKB and telomerase. *World J Gastroenterol* 2003; 9 (10): 2362-2365. <https://doi.org/10.3748/wjg.v9.i10.2362>

تحويل ودراسة النشاط الحيوي للكيوتوسان مع مركبات تحتوي على مجموعة الأزو

رويدة سمير سعيد، هدى احمد حسن، ضفاف فلاح حسن، منى سمير سعيد

قسم الكيمياء، كلية التربية للعلوم الصرفة ابن الهيثم، جامعة بغداد، بغداد، العراق.

الخلاصة

في البحث الحالي تم تحضير ودراسة النشاط الحيوي لسلسلة من البوليمرات الجديدة المحورة من الكيوتوسان مع مركبات تحتوي على مجموعة الأزو. في البداية تم تحضير ملح الديازونيوم من تفاعل 3,3'-dimethyl-[1,1'-biphenyl]-4,4'-diamine مع حامض الهيدروكلوريك المركز و تترتير الصوديوم. ثم تفاعل الازدواج بين ملح الديازونيوم مع الديهايدات اروماتية معوضة لإنتاج مشتقات الأزو (6-1). أزو شف بيس كيوتوسان(7-12) والتي حضرت من تفاعل الكيوتوسان مع مشتقات الأزو (1-6) في مذيب الايثانول مع قطرات من حامض الخليك الثلجي. التحويلات الهيكلية في موقع المجموعة الأمينية لحلقة الكيوتوسان (المرتبطة بمجموعة الأزو النشطة بايولوجيا) كان من المتوقع أن يعطي مشتقات جديدة(7-12) ذات مجموعة واسعة من الأنشطة البيولوجية.

تم استخدام تحليلات ¹H-NMR, FT-IR الطيفية والمسح الضوئي بالمجهر الإلكتروني لمسح الانبعاثات الميدانية لتوضيح هيكل هذه المركبات علاوة على ذلك، تم فحص بعض المركبات الجديدة المحضرة والكيوتوسان المحور للأنشطة المحتملة المضادة للبكتيريا ضد نوعين من البكتيريا: البكتيريا السالبة E.coli والبكتيريا الموجبة Staphylococcus aureus. أظهرت كل هذه البوليمرات المحورة المستهدفة نشاطاً عالياً مقارنة بالبنسلين (المستخدم كمضاد حيوي مرجعي). وخصوصاً البوليمر المحور رقم (7) الذي أظهر تثبيطاً عالياً ضد كلا النوعين من البكتيريا Staphylococcus aureus و E.coli. تم دراسة النشاط المضاد للسرطان للكيوتوسان المحور (7) ضد خط خلايا سرطان الثدي البشري (MCF-7) باستخدام تقنية 3-(4,5-ثنائي ميثيل ثيازول-2-يل)-2,5-بروميد ثنائي فينيل تينرازوليوم (MTT) ومقارنته مع خط الخلايا الطبيعية (خط الخلايا الكبدية البشرية WRL-68) حيث أظهر البوليمر (7) تثبيطاً عالياً للخلايا السرطانية وأقل سمية للخلايا الطبيعية

الكلمات المفتاحية: مركبات الأزو، كيوتوسان، ملح الديازونيوم، دراسة المجهر الإلكتروني لمسح الانبعاثات الميدانية، خط خلايا سرطان الثدي البشري، قواعد شف.